



CONSEIL AFRICAIN ET MALGACHE POUR L'ENSEIGNEMENT SUPÉRIEUR

01 BP 134 OUAGADOUGOU 01 (BURKINA FASO)  
TEL (226) 25 36 81 46 - FAX (226) 25 36 85 73 - Email: [comes@lecomes.org](mailto:comes@lecomes.org)

# Article 2

**Titre:** Physico-Mechanical and Acoustic Characterization of Mimusops andongensis Wood from Benin in West Africa

**Auteurs :** M. C. Hounlonon, **C. A. Kouchadé**, A. Mèdéhouéno, V. Gohoungo et B. B. Kounouhéwa,

**Journal:** American-Eurasian J. Agric. & Environ. Sci., Vol 22, N°2.

**Lien :** [https://www.idosi.org/aejaes/jaes22\(2\)22/2.pdf](https://www.idosi.org/aejaes/jaes22(2)22/2.pdf)

**Bases de données d'indexation:** Chemical Abstracts (CAS Source Index – CASSI), CABI

**Nom :** **KOUCHADE**

**Prénoms :** **Adéyèmi Clément**

**Institution :** Université d'Abomey-Calavi

**CTS:** Sciences et Techniques de l'Ingénieur


**Tel:** +229 94398889

**email :** [ckouchade@yahoo.fr](mailto:ckouchade@yahoo.fr)



[AEJAES](#) | [Journals](#) | [For Authors](#) | [Publications Ethics](#) | [Peer Review](#) | [Contact Us](#)

### Call for Papers

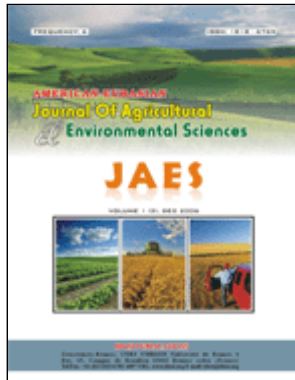

### Amer-Eurasian Journal of Agricultural & Environmental Sciences

- :: Abstracting/Indexing
- :: CABI
- :: DOAJ
- :: EBSCO Inc.
- :: e-journals Database
- :: Agriculture Resources
- :: etc.

[AEJAES](#) | [Aims & Scope](#) | [Editorial board](#) | [On-line Issues](#)

**CAS Source Index (CASSI) Search Result**Displaying Record for Publication: [American-Eurasian Journal of Agricultural & Environmental Sciences](#)

<b>Entry Type</b>	Active Serial
<b>Title</b>	American-Eurasian Journal of Agricultural & Environmental Sciences
<b>Abbreviated Title</b>	Am.-Eurasian J. Agric. Environ. Sci.
<b>CODEN</b>	AJAECB
<b>ISSN</b>	1990-4053
<b>Language of Text</b>	English
<b>Summaries In</b>	English
<b>History</b>	v1 n1 Jan./Apr. 2006+
<b>Publication Notes</b>	Avail. from Internet at URL: <a href="http://www.idosi.org/aejaes/aejaes.htm">http://www.idosi.org/aejaes/aejaes.htm</a>
<b>Publisher Name</b>	International Digital Organization for Scientific Information

**Disclaimer**

---

## Physico-Mechanical and Acoustic Characterization of *Mimusops andongensis* Wood from Benin in West Africa

<sup>1,2</sup>Montcho Crépin Hounlonon, <sup>1,2</sup>Clément Adéyèmi Kouhadé,  
<sup>1</sup>Alexis Mèdèhouénou, <sup>1,2</sup>Vincent Gohoungo and <sup>1,2</sup>Basile B. Kounouhéwa

<sup>1</sup>Laboratoire de Physique du Rayonnement (LPR), Département de Physique, Faculté des Sciences et Techniques, Université d'Abomey-Calavi, BP 526 Cotonou, République du Bénin  
<sup>2</sup>Formation Doctorale Sciences des Matériaux (FDSM) de l'Ecole Doctorale Sciences Exactes et Appliquées (EDSEA), Université d'Abomey-Calavi, BP 526 Cotonou, République du Bénin

**Abstract:** Wood is a multifunctional anisotropic biomaterial. It is used in various fields, including the craft industry and the construction of structural works. In heavy construction or in wetlands, species with high technological characteristics are sought after. *Mimusops andongensis* is a species empirically identified as having good technological properties. However, none of these reference characteristics are known. Thus, to fill this gap, we tested 500 mm × 20 mm × 20 mm prismatic specimens of *Mimusops andongensis* wood using CIRAD-Forest's acoustic BING (Beam Identification by Non-destructive Grading) method to determine density  $\rho$ , Young's modulus E and shear modulus G, internal friction  $\tan\delta$  and then evaluated the specific stiffness modulus  $E/\rho$ . On other 20 mm side cubic specimens, we evaluated the physical properties. From this investigation, *Mimusops andongensis* timber is a heavy to very heavy timber with high modulus. Its volume shrinkage is moderate with low tangential and medium radial shrinkage. Its low shrinkage anisotropy predicts low distortional and splitting deformation. Its specific stiffness is high on the order of  $(18 \pm 1)$  GPa for a low internal friction of  $(0.64 \pm 0.15) \times 10^{-2}$ . In a humid environment, the loss of mechanical properties, by increasing its moisture content, even by 20 %, leaves *Mimusops andongensis* timber in the range of woods with very appreciable properties. Referring to the highly valued species, it can be used in works both in structure and acoustics.

**Key words:** Infra-density • Heartwood • Tropical Hardwood • Compression • Bending • Moisture Content

### INTRODUCTION

Trees have a multifunctional role and wood from them is a highly valued material. In the implementation of projects for the construction of tourist structures on stilts, wood species with high technological characteristics are sought. Among these species identified, we can mention *Mimusops andongensis*.

The genus *Mimusops* belongs to the class Magnoliopsida, order Ebenales/Ericales and to the family Sapotaceae. *Mimusops andongensis* Hiern is a Wild Edible Fruit Tree (WFET) listed among food and medicinal

species. It represents a multiple-use species for local populations [1-4]. This predisposes it to a potential threat. Studies conducted in Benin, following the criteria of the International Union for Conservation of Nature (IUCN), have classified *Mimusops andongensis* Hiern as a rare and threatened species in Benin [5-8]. The rarity of this species has certainly resulted in its non-description in the analytical flora of Benin while *Mimusops kummel* is well presented [9].

In national languages, *Mimusops andongensis* Hiern is called bohê [10] or afoutin in Fon [11] and égui ochéé in Holli [10], for others in Fon it is called kinwi and in

**Corresponding Author:** Montcho Crépin Hounlonon, Laboratoire De Physique Du Rayonnement (LPR),  
Département De Physique, Faculté des Sciences et Techniques & Formation Doctorale Sciences  
des Matériaux (FDSM) de l'Ecole Doctorale Sciences Exactes et Appliquées (EDSEA),  
Université d'Abomey-Calavi, BP 526 Cotonou, République du Bénin.  
Tel: +229 97504727.

Nagot igui odu or ochèdo. *Mimusops andongensis* and *Mimusops kummel* are found in semi-deciduous forests and riparian forests which represent their natural habitat [5, 12]. *Mimusops andongensis* and *Mimusops kummel* also occur from north to south of Benin along three bioclimatic zones [13]. Hounkpèvi *et al.* studying the structure and ecology of two other species (*Diospyros mespiliformis* Hochst. ex A. DC. and *Dialium guineense* Willd) from the Massi Reserve in Lama, noted among others the presence of *Mimusops andongensis* with high heights [14]. *Mimusops andongensis* is a small to medium sized shrub or tree up to 20 m tall, containing latex. It has a dense, heavily branched crown [15]. The bole can measure up to 100 cm in diameter but usually much less. In southern Benin, *Mimusops andongensis* is locally quite common in periodically flooded forests on heavy clay soils, where it represents about 3 % of the trees [15]. *Mimusops andongensis* wood is a hardwood used in forestry and for fishing. It is locally highly valued in both Benin and Nigeria [15]. It is used in construction, in dugout canoes, axe handles and carving, charcoal production and as fuel wood [11, 16, 17]. The bark, roots, leaves and latex from the bark are exploited to treat malaria, toothache, skin infections and as a penile stimulant, etc [1, 17-19]. The latex of *Mimusops andongensis* is still used to flavour palm wine. The fruit is used as a substitute for chewing gum [15]. *Mimusops andongensis* is a species known to have magical powers [1, 20] and is one of the potential commercial species in the Central Nucleus of the Lama Forest under ONAB management [21]. Sinasson *et al.* [11] determined the uses, local knowledge and abundance mutations of *Mimusops* species in Benin. Sinasson *et al.* [13] also investigated ecological patterns and the effectiveness of protected areas in preserving habitats for *Mimusops* species under climate change. Similarly, Sinasson *et al.* [22] evaluated the structure, stability and plant morphology of *Mimusops andongensis* and *Mimusops kummel* under different socio-ecological constraints in Benin. Unfortunately, all these studies on *Mimusops andongensis* did not address the technology of its wood. That is why, in our logic to have a good data base on the technological characteristics of the woods exploited in Benin, the wood of *Mimusops andongensis* was the subject of physical, mechanical and acoustic characterization tests.

The objective of this study was therefore to evaluate the physical-mechanical and acoustic characteristics of *Mimusops andongensis* wood from Benin. The properties

obtained are compared with those of other highly prized species in order to deduce the possible uses of *Mimusops andongensis* wood. Finally, the influence of humidity on the characteristics of *Mimusops andongensis* wood was studied.

The main characteristics determined are density, infra-density, volume shrinkage, radial shrinkage, tangential shrinkage, modulus of elasticity in compression, modulus of elasticity in bending, shear modulus, internal friction and specific rigidity.

## MATERIALS AND METHODS

For the investigation, we used, the plant material consisted of *Mimusops andongensis* specimens cut from a foot taken at plot 22a of Massi forest. This forest is under ONAB (National Timber Office of Benin) management in Lama in southern Benin. Plot 22a is at the edge of the central core. The tree is apparently young with a diameter of about 32 cm at man's height. The prohibitions on the species have not allowed more trees to be harvested. The wood is very poorly hardened with a heartwood percentage of about 48 %. Figure 1 shows the trunk and a log of the *Mimusops andongensis* tree. From this trunk, in addition to the 2×2×50 cm prismatic specimens (Figure 2) cut for mechanical measurements, 2 cm edge cubic specimens were also cut for evaluation of physical parameters (density and shrinkage).

For the mechanical measurements, the method of mechanical characterization used is the non-destructive one based on the BING device (Beam Identification By Non-Destructive Grading) of CIRAD-Forêt whose principle was the subject of work of Brancheriau [23]. The device is based on the theory of beams and is based on the Bernoulli and Timoshenko models. It uses frequency analysis of vibration signals by Fast Fourier Transform (FFT) and has been used in the work of Ahmed and Adamopoulos [24] and Hounlonon *et al.* [25]. BING is used to obtain the longitudinal flexural and compressive modulus of elasticity, shear modulus, internal friction and specific stiffness, among others.

The determination of physical parameters such as shrinkage, density and infra-density or basal density were done according to the AFNOR standard as described by the *Memento du Forestier* [26], Gérard *et al.* [27], Kouchadé *et al.* [28] and Tonouéwa *et al.* [29, 30]. The tests were performed on standardized specimens without defects. The cubic specimens sized for the physical tests were immersed in water until fully saturated.

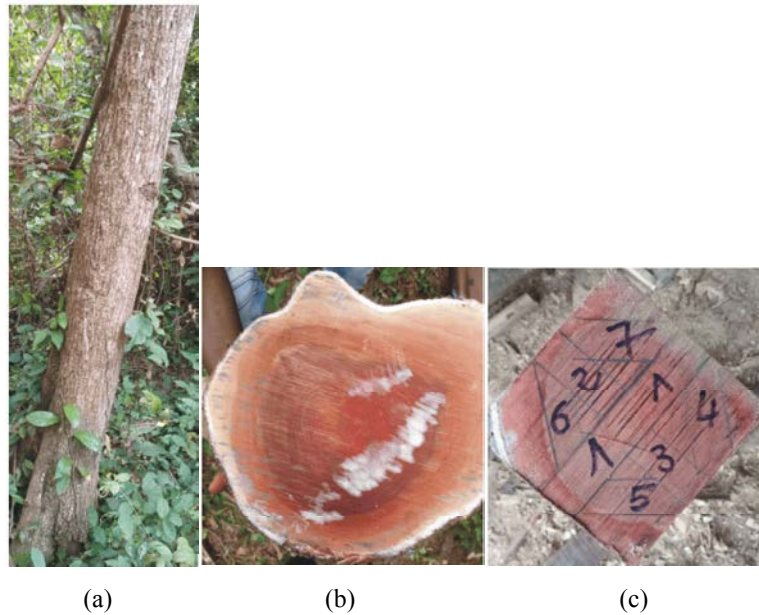


Fig. 1: Trunk (a), washer (b) and top view (c) of *Mimusops andongensis* trunk shaped for debitage joinery



Fig. 2: Some specimens of *Mimusops andongensis* wood

At saturation, the following measurements were taken on each specimen: the saturated volume by the buoyancy method, the radial, tangential, axial or longitudinal dimensions using an electronic caliper of 0.01 mm precision. The specimens were then stabilized in a temperature-controlled oven at 103°C. At the end of each stabilization and at the end of the drying process, the anhydrous mass, also called dry mass, was measured using a 0.01 g precision electronic balance. Also, the dimensions in the orthotopic directions of each sample were measured.

The data obtained from BING or by calculation allowed us to obtain the descriptive statistics results presented in Table 1.

## RESULTS

**Physical, Mechanical and Acoustic Properties of *Mimusops andongensis*:** The tests carried out on 20 samples allowed to determine the average values and standard deviations of the physical and mechanical

Table 1: Physical, mechanical and acoustic properties of *Mimusops andongensis*

Air-dry density ( $\text{kg.m}^{-3}$ )	<i>m</i>	1, 017
	<i>e</i>	58
Anhydrous density ( $\text{kg.m}^{-3}$ )	<i>m</i>	948
	<i>e</i>	47
Infra-density ( $\text{kg.m}^{-3}$ )	<i>m</i>	854
	<i>e</i>	62
Total volume shrinkage (%)	<i>m</i>	10.01
	<i>e</i>	2.43
Tangential shrinkage $R_T$ (%)	<i>m</i>	6.35
	<i>e</i>	1.79
Radial shrinkage $R_R$ (%)	<i>m</i>	4.16
	<i>e</i>	0.94
Shrinkage anisotropy $R_T/R_R$	<i>m</i>	1.53
	<i>e</i>	0.25
Modulus of elasticity in bending (MPa)	<i>m</i>	18, 470
	<i>e</i>	1, 828
Modulus of elasticity in compression (MPa)	<i>m</i>	16, 749
	<i>e</i>	1, 250
Shear modulus (MPa)	<i>m</i>	1, 323
	<i>e</i>	255
Specific modulus of elasticity ( $\text{GPa}$ or $\text{MPa.kg}^{-1}.\text{m}^3$ )	<i>m</i>	18
	<i>e</i>	1
Internal friction $\tan\delta$ ( $10^{-2}$ )	<i>m</i>	0.64
	<i>e</i>	0.15

m: mean e: standard deviation

parameters presented in Table 1. Thus, the wood of *Mimusops andongensis* has an air-dry density of  $(1,017 \pm 58) \text{ kg.m}^{-3}$ , an anhydrous density of  $(948 \pm 47) \text{ kg.m}^{-3}$  and an infra-density of  $(854 \pm 62) \text{ kg.m}^{-3}$ . Regarding

shrinkage, *Mimusops andongensis* has average volume shrinkage of less than 13 %. The tangential shrinkage of  $(6.35 \pm 1.79)$  % is relatively low as well as the radial shrinkage which is  $(4.16 \pm 0.94)$  %. The shrinkage anisotropy remains low and is  $(1.53 \pm 0.25)$ . Thus, in terms of mechanical stiffness, *Mimusops andongensis* has longitudinal flexural  $(18470 \pm 1,828)$  MPa and compressive  $(16,749 \pm 1,250)$  MPa moduli. Its specific stiffness is  $(18 \pm 1)$  GPa. Its shear modulus is  $(1,323 \pm 255)$  MPa. They are, as well as its internal friction, in the order of those of tropical hardwoods. Its degree of dissipation of vibrational energy by internal friction) that is internal friction  $\tan\delta$  is very low and less than  $10^{-2}$ .

## DISCUSSION

**Mimusops Andongensis Wood Compared to Woods of High Technological Value in Benin:** From our research in the literature, the physical-mechanical and acoustic properties of *Mimusops andongensis* have not been studied.

*Mimusops andongensis* is a heavy wood, even very heavy. Cross-referencing our results with the characteristics of other species, the density of *Mimusops andongensis* remains far better than that of highly prized species such as *Tectona grandis* ( $800 \text{ kg.m}^{-3}$ , [31]), *Acacia auriculiformis* ( $825 \text{ kg.m}^{-3}$ , [25]), *Azelaia africana* ( $800 \text{ kg.m}^{-3}$ , [32]), *Diospyros mespiliformis* ( $900 \text{ kg.m}^{-3}$ , [32]) and *Erythroleum ivorensis* ( $910 \text{ kg.m}^{-3}$ , [32]), which have a relatively high density

Investigation on timber species highly valued in North Benin such as *Anogeissus leiocarpus* and *Pseudocedrela kotschy* showed that their infra-densities are respectively  $911.0$  and  $824.86 \text{ kg.m}^{-3}$  [29] and similar to that of *Mimusops andongensis*. Compared to other popular species in Benin, *Mimusops andongensis* is noble as its infra-density is much higher than that of other species such as *Azelaia africana*, *Pterocarpus erinaceus*, *Khaya senegalensis*, *Milicia excelsa*, *Gmelina arborea*, *Diospyros mespiliformis*, *Tectona grandis*, *Isobertia doka*, whose infra-densities range from  $560.29$  to  $795.02 \text{ kg.m}^{-3}$  [29]. The infra-density of *Mimusops andongensis* is largely above those of *Acacia auriculiformis* which has values between  $496$  and  $705 \text{ kg.m}^{-3}$  [30].

According to wood construction professionals, some wood species are very appreciating in heavy construction, especially in contact with the ground or water. Among these species, there are *Diospyros mespiliformis* (African Ebony), *Anogeissus leiocarpus*, *Erythroleum ivorensis* (Tali), *Manilkara multinervis* and

*Cylicodiscus gabunensis*, ... Regardless of the density of their wood, Beninese foresters have noted the use of *Manilkara spp.* for the construction of piles in pile dwellings; of *Mimusops andongensis* for the construction of huts or straw huts in humid environments, even in contact with the ground.

Tali, a substitute for *Lophira alata* (Azobé) is a species used for constructions in humid environments or in contact with the ground [32]. It is found, in hydraulic works, heavy carpentry, bridges, heavy or industrial flooring, sleepers, posts [32].

Of use class 4 like Tali, ebony wood is used in guitar making [33], in tablet making, instrument making, luxury cabinet making, carving, turned items, wind instruments and as a resilient wood in tool handles [32].

*Manilkara spp* is a heavy wood with good natural durability that can be used in structural works such as musical instrument making, exterior construction, sleepers, flooring (heavy floor construction), boat building and marine works [34-37]. It is used intuitively or empirically by the inhabitants of lake villages in Benin as piles for pile constructions.

*Anogeissus leiocarpus* is one of the most exported wood species from Benin [38]. It is a very useful timber in works both in structure and floor construction as well as heavy works [29, 39, 40].

With a use class of 5, *Cylicodiscus gabunensis* is a wood species used in construction in Benin [41] and can also be in hydraulic works in maritime environment, in sculpture, in heavy carpentry, as crossbeam, in bridge construction, as posts, parquet, floor or in the confection of turned articles [32]. In Korea, it is used for heavy-duty flooring such as factories and warehouses, for decking and wooden floors [42]. *Cylicodiscus gabunensis* is a moderately stable to low stable wood species [32, 34].

Table 2 presents some properties of these wood species with high technological potential for high-stress structures. From the data of this table crossed with our parameters found, *Mimusops andongensis* is a valuable wood species. Thus, in terms of mechanical stiffness, *Mimusops andongensis* has high longitudinal moduli of elasticity in bending and compression as predicted by its density. Its shear modulus is moderately high. According to the reference of Gerard *et al.* [27, 32], the high modulus wood of *Mimusops andongensis* is in the range of Tali wood which has a longitudinal modulus of elasticity of  $19,490 \text{ MPa}$  [32] and wood species of *Anogeissus leiocarpus*, *Diospyros mespiliformis*, *Cylicodiscus gabunensis*, *Manilkara spp* (Table 2). *Mimusops andongensis* has a lower internal friction ( $\tan\delta$ ) than African ebony used in

Table 2: Physico-mechanical properties of some popular species according to the literature

	Authors	<i>Anogeissus leiocarpus</i>	<i>Diospyros mespiliformis</i>	<i>Cylicodiscus gabunensis</i>	<i>Manilkara</i> spp.
Density (kg.m <sup>-3</sup> )	[39]	1, 150 ± 50			
	[40]	1, 150			
	[32]		900 ± 60	910 ± 100	
	[41]			1, 100	
	[34]			950	
	[42]			Sapwood (770-890) Heartwood (1, 160-1,230)	
	[37]				870-950
	[36]				1, 058-1, 140
	[45]				900-1, 150
	Modulus of elasticity (MPa)	[39]	17, 512 ± 8, 009		
[40]		10, 117			
[32]			15, 500 ± 3500	22,260 ± 3,348	
[33]			17, 680-23, 9200		
[34]				16, 600	
[37]					10, 800-19, 600
[36]					16, 758-25, 650
[35]					17, 271 ± 2253
Tangential shrinkage (%)	[29]	6.57 ± 0.14	6.59 ± 0.128		
	[32]		11.0 ± 0.5	7.9 ± 1.0	
Radial shrinkage (%)	[29]	6.18 ± 0.12	4.77 ± 0.136		
	[32]		7.0 ± 0.2	5.8 ± 0.6	
Shrinkage anisotropy	[29]	1.26 ± 0.04			
	[32]		1.6	1.4	
Volume shrinkage (%)	[29]	14.71 ± 0.25	11.39 ± 0.271		
	[39]	9.17 ± 3.64			

both construction and instrument making [32, 33]. *Mimusops andongensis* has good specific stiffness better than African ebony but lower than Tali. African Ebony wood with its specific stiffness of 17 GPa and internal friction of  $0.81 \cdot 10^{-2}$ , Tali with its specific stiffness of about 21 GPa and internal friction of  $0.97 \cdot 10^{-2}$  [32] remain more dissipative of vibrational energy by internal friction than *Mimusops andongensis* wood.

Dimensional changes below the fibers saturation point FSP affect the stability of wood products [43]. Shrinkage anisotropy is a major determinant of wood quality. Too high a value of this variable can lead to distortion or splitting [44]. The shrinkage anisotropy of *Mimusops andongensis* of 1.53 is lower than those of class 4 species such as Tali and African ebony which have anisotropy of 1.6. The propensity for deformation (distortion or splitting) of *Mimusops andongensis* is low. Volume shrinkage of *Diospyros mespiliformis* (Table 2) and *Erythrophleum ivorensis* (Tali) whose transverse linear shrinkage are  $R_T (8.4 \pm 1.2) \%$ ;  $R_R (5.1 \pm 1.4) \%$  [32] have higher shrinkage coefficients than *Mimusops andongensis*. *Mimusops andongensis*, due to its shrinkage anisotropy, will deform less than Tali but slightly more than *Anogeissus leiocarpus* from Benin and almost in the same range as African Ebony and *Cylicodiscus gabunensis*.

**Possible Uses of *Mimusops andongensis*:** Since the values of the different properties of a wood species depend on age, ecology or heredity [32, 46], it is certain that there are woods of *Mimusops andongensis* with better characteristics than the one in this study. As it is and taking into account the good technological properties of *Mimusops andongensis* similar in some cases and better in others to those of the previously mentioned species, its wood would have broadly similar applications. Its character as a heavy wood having been proven, its use in forestry and for fishing, construction, in dugouts, axe handles and carving, charcoal production and as energy wood [11, 16, 17] is well confirmed. The good values of the characteristics obtained compared to those of highly valued species such as teak, African ebony, veneer and iroko and species with high technological value, above, sufficiently prove its very good potential to be used in heavy and light constructions as noted by Lemmens who reports its use in construction [15]. It is, at the present stage, very likely to be used in structural works as the highly prized species and species of class of use 4 or 5. The distortion and splitting of this wood is less than that of Tali, but almost of the same range as African Ebony and *Cylicodiscus gabunensis*. However, its wood warps slightly more than *Anogeissus leiocarpus* from Benin.

Its dark pink to red colored texture, high density and modulus, good specific rigidity and low damping coefficient also suggest it to be a good resonance wood in instrument making or in auditorium and concert hall construction [47]. Its overall medium shrinkage and low shrinkage anisotropy reassures that it has good potential for use in various sculptures and construction in high moisture gradient environments.

But what is the influence of humidity on the characteristics of its wood and what are the great opportunities of its real use?

**The Influence of Moisture on the Physical, Mechanical and Vibratory Properties of Wood:** As *Mimusops andongensis* is already used in traditional structures in contact with the ground or water or on piles in a humid environment, it is useful to study the effect of water on its physical-mechanical parameters. Indeed, humidity can generate transient or permanent modifications of the properties of the wood material. Moisture variation can generate transient gradients in water content that with the wood piece will induce internal stresses [48].

The density of wood has a positive influence on the shear strength of tropical hardwoods [49] and on other mechanical properties such as modulus of elasticity [23]. The increase in moisture content leads to a decrease in specific density and mechanical properties [50]. All mechanical properties of wood grow with decreasing moisture content below the fiber saturation point (FSP) approximately at 30 % moisture content [51- 53]. The modulus of elasticity decreases with relative humidity and the modulus of rupture reaches a maximum at 54.3 % RH or 8 - 9 % moisture content and then decreases with relative humidity thereafter [54]. The overall decreasing trend observed for the elastic modulus was also obtained by Gerhards [51]. Obataya *et al.* [50] reported on Sitka spruce (*Picea sitchensis*) wood that the modulus of elasticity drops overall with increasing moisture content and the loss of modulus of elasticity can be about 20 % between 0 and 30 % moisture content and about 15 % between 12 % and 30 % moisture content. Microscopic study of microfibrils, vessels and cells of wood of the same species confirmed the above dual trends for several quantities: specific gravity, modulus of elasticity and shear modulus have the same trends and internal friction an opposite trend [50]. According to the same study, from 9.6 % of moisture content onwards, an overall decreasing trend is observed for the modulus of elasticity and the shear modulus.

Also, for the vibrational properties of wood, a decreasing trend in specific stiffness  $E/\rho$  and a growth in internal friction  $\tan\delta$  are observed as the equilibrium water content increases [50]. However, the degree of influence of moisture content differs in the orthotropic directions (L, R, T) of the wood [55]. There are values of water content for which the internal friction is minimal [50, 53]. Outside of this minimum, internal friction increases as the moisture content drops to zero or above the fiber saturation point [53]. The moisture content for which internal friction is minimal varies with temperature [53]. The higher the temperature, the more minimal the water content value and tends to zero [53]. Obataya *et al.* [50] also noted that internal friction increases from 0 to 1 % moisture content, decreases from 1 to 6 % moisture content and then increases again from 6 to 30 % moisture content. For the last phase of growth, the internal friction varies from  $5.5 \cdot 10^{-3}$  to about  $9.7 \cdot 10^{-3}$  or about 75 %. According to the same authors, on the basis of a microscopic study of the cells, fibrils and vessels of *Picea sitchensis* wood, the internal friction increases as the moisture content of the wood increases from 9.6 % moisture content.

Generally high shrinkage is associated with high densities. The size and shape of the wood piece can influence the shrinkage, as can the degree of drying, which can affect the shrinkage for some wood species [53]. With moisture variation, the relationship between moisture content and shrinkage is not linear, but overall, shrinkage decreases as moisture content increases. Above the FPL, no wood undergoes dimensional deformation, so it is clear that *Mimusops andongensis* can withstand the wet environment although its mechanical characteristics will decrease if it is completely wet. Referring to the study of Obataya *et al.* [50] on *Picea sitchensis*, its use in a humid environment could generate, in the critical case, a loss of mechanical characteristics, in particular, of the modulus of elasticity of only 15 to 20 %. In this range of loss of mechanical characteristics, the average modulus of elasticity would be in equal variation between 14, 776 and 15, 700 MPa bringing the *Mimusops andongensis* pile in the woods of medium modulus (MOE < 15,000 MPa) or heavy modulus (MOE > 15,000 MPa) [27]. Such characteristics, cumulated with the other characteristics in the same range of variation in a situation of humidity or shrinkage-swelling would be limited [53], *Mimusops andongensis* would make a species very appreciated in terrestrial constructions as in situations of high stress as in wetlands, lacustrine or in contact with water. Its natural habitat of wetlands and riparian forest [15] would be of these assets.

It is to be hoped that following this work, studies of natural durability, behaviour at different moisture contents, thermal behaviour and behaviour in the face of mineral salts specific to our aquatic and marine environments will be carried out to confirm its average shrinkage, its high modulus and its character as a heavy or even very heavy wood due to its density.

### CONCLUSIONS

The study of the physico-mechanical and acoustic characteristics of *Mimusops andongensis* with respect to the characteristics of prized species or woods of high technological value in Benin such as Tali, African Ebony, *Cylicodiscus gabunensis*, *Anogeissus leiocarpus*, *Manilkara multinervis* reveals its high potential because of its high technological characteristics.

*Mimusops andongensis* wood, previously unknown technologically, is a heavy wood with high modulus and low tangential shrinkage, volume shrinkage and radial shrinkage overall. This wood has low shrinkage anisotropy with a high mechanical stiffness for a very low vibration energy dissipation. It is a heavy or even very heavy wood due to its density which even in a humid environment would have a maximum loss of 20%. Such a loss would still guarantee good technological properties. These properties of *Mimusops andongensis* show its good potential in structural works in both dry and wet environments. It is to be wished studies of durability, thermal behaviour and preservation treatment to complete its technological characteristics. It would also be advisable to further explore the ecology and silviculture of the species to work on its domestication as a guarantee of a planned multifunctional *Mimusops andongensis*.

### ACKNOWLEDGEMENTS

- To the Direction Générale des Eaux, Forêts et Chasses (DGEFC) and the Office National des Bois (ONAB) of Benin for agreeing to allow the cutting of the *Mimusops andongensis* sample for the test.
- To the « Agence Nationale de Promotion des Patrimoines et de Développement du Tourisme » of Benin and its Director General.
- To Mr. Akouta, President of the interprofessional association of the wood sector for the accompaniment in the research of the *Mimusops andongensis* and the species with strong technological potentiality marketed in Benin.

### REFERENCES

1. Lokonon, E.B., 2008. Structure and ethnobotany of *Dialium guineense* Willd, *Diospyros mespiliformis* Hochst. Ex A. Rich. And *Mimusops andongensis* Hiern. In populations in the Central Nucleus of the Classified Forest of Lama (South-Benin). Thesis of Agricultural Engineer, FSA/UAC, pp: 58.
2. Vitoule, E.T., T. Houehanou, B. Kassa, A.E. Assogbadjo, R.G. Kakai, J. Djego and B. Sinsin, 2014. Endogenous knowledge and human disturbance impact on abundance of two underutilized wild edible tree species in southern Benin. QScience Connect 2014:15. <http://dx.doi.org/10.5339/connect.2014.15>.
3. Agbahoungba, S., A.E. Assogbadjo, F.J. Chadare, R. Idohou, V.K. Salako, E.E. Agoyi and R.L.G. Kaka, 2016. Ecological diversity and conservation of wild edible fruit trees in the Lama Forest Reserve in Benin. Bois For. Trop., 339: 53-65.
4. Agbahoungba, S., A.E. Assogbadjo, E.E. Agoyi and B. Sinsin, 2019. Diversity and Current Spatial Distribution of Wild-Edible Fruit Trees Species in the Lama Forest Reserve in Benin, International Journal of Fruit Science, 19: 13-28, DOI: 10.1080/15538362.2018.1501633.
5. Adomou, A.C., 2005. Vegetation Patterns and Environmental Gradients in Benin: Implications for Biogeography and Conservation (Ph.D. dissertation). Wageningen University, Wageningen, Netherlands. [\\_qhttps://edepot.wur.nl/121707\\_r](https://edepot.wur.nl/121707_r).
6. Adomou, A.C., B. Sinsin, A.A. Akoègninou and J. Van Der Maesen, 2010. Plant species and ecosystems with high conservation priority in Benin. Systematics and Conservation of African Plants. Kew: Royal Botanic Gardens.
7. ONAB, 2011. Master plan for the development and management of the central core of the lama classified forest 2011-2020. 87.
8. Neuenschwander, P., B. Sinsin and G. Goergen, 2011. Nature Conservation in West Africa: Red List for Benin. Nature Conservation in West Africa: Red List for Benin. International Institute of Tropical Agriculture, Ibadan, Nigeria, pp: 365.
9. Akoègninou, A., W.J. Van Der Burg and L.J.G. Van Der Maesen, 2006. Analytical Flora of Benin. Cotonou and Wageningen: Backuys Publishers.
10. Affoukou, C., 2013. Ecology, structure and importance of *Mimusops andongensis* Hiern in the classified forest of Lama in South-Benin, Dissertation of design engineer, Ecole Polytechnique d'Abomey-Calavi (EPAC), University of Abomey-Calavi (UAC).

11. Sinasson, G.K.S., C.M. Shackleton, A.E. Assogbadjo and B. Sinsin, 2017. Local Knowledge on the Uses, Habitat and Change in Abundance of Multipurpose Mimusops Species in Benin, Economic Botany.
12. Cheke, R.A., 2001. Benin. In: Fishpool, L.D.C., Evans, M.I. (Eds.), Important Bird Areas in Africa and associated islands: Priority sites for conservation. Pisces Publications and Bird Life International (Bird Life Conservation Series No. 11), Newbury and Cambridge, UK, 93-98, <http://datazone.birdlife.org/userfiles/file/IBAs/Africa/CntryPDFs/Benin.pdf>.
13. Sinasson, S.G.K., C.M. Shackleton, O. Oscar Teka and B. Sinsin, 2021. Ecological patterns and effectiveness of protected areas in the preservation of Mimusops species' habitats under climate change. *Global Ecology and Conservation* 27, e01527.
14. Hounkpèvi, A., A.S.I. Yévidé, J.C. Ganglo, J.L. Devineau, A.H. Azontonde, V. Adjakidje, E.K. Agbossou and B.D. Foucault, 2011. Structure and ecology of the *Diospyros mespiliformis* Hochst. ex A. DC. and *Dialium guineense* Willd. Forest of the Massi Reserve (La Lama), Benin. *BFT*, 308: 33-46.
15. Lemmens, R.H.M.J., 2005. *Mimusops andongensis* Hiern. [Internet] Record from PROTA4U. Louppe, D., Oteng-Amoako, A.A., Brink, M. (Eds.), PROTA (Plant Resources of Tropical Africa/Ressources Végétales de l'Afrique Tropicale), Wageningen, Netherlands. [\\_qhttp://www.prota4u.org/search.asp\\_r](http://www.prota4u.org/search.asp_r). Accessed 02 January 2022.
16. Lemmens, R.H.M.J., E.A. Omino and C.H. Bosch, 2010. Timber from tropical Africa. Conclusions and recommendations based on PROTA 7(1): "Timber 1?". [Translation of: Timbers of Tropical Africa. Conclusions and recommendations based on PROTA 7(1): 'Timbers 1'. 2009]. PROTA Foundation, Nairobi, Kenya, pp: 92.
17. Soro, D., M.W. Kone and K. Kamanzi, 2010. Evaluation of the Antimicrobial and Free Anti-Radical Activities of some Bioactive Taxa from Ivory Coast. *European Journal of Scientific Research*, ISSN 1450-216X, 40: 307-317.
18. Burkill, H.M., 1985. The Useful Plants of West Tropical Africa. Royal Botanic Gardens, Kew, UK.
19. Louppe, D., A.A. Oteng-Amoako and M. Brink, 2008. Plant Resources of Tropical Africa. *Timbers 1*, PROTA, 7(1): 565-566.
20. Arbonnier, M., 2002. Shrub trees and lianas of the dry zones of West Africa. CIRAD-MNHN, pp: 573.
21. Emrich, A., A. Horst, K. Küppers and H.J. Sturm, 1998. Integrated ecological assessment of the Lama Natural Forest in the Republic of Benin. Synthesis report. ONAB-KfW GTZ. Cotonou, Benin, pp: 74 + annexes.
22. Sinasson, S.G.K., C.M. Shackleton and B. Sinsin, 2021. Nationwide Assessment of Population Structure, Stability and Plant Morphology of Two Mimusops Species along a Social-Ecological Gradient in Benin, West Africa. *Forests*, 12: 1575. <https://doi.org/10.3390/f12111575>.
23. Brancheriau, L., 2002. Mechanical expertise of sawn timber by vibration analysis in the acoustic domain. PhD Thesis, Ecole supérieure de mécanique de Marseille, France.
24. Ahmed, S.A. and S. Adamopoulos, 2018. Acoustic properties of modified wood under different humid conditions and their relevance for musical instruments. *Applied Acoustics*, 140: 92-99. <https://doi.org/10.1016/j.apacoust.2018.05.017>.
25. Hounlonon, M.C., A.C. Kouchadé and B.B. Kounouhéwa, 2021. Physical and Mechanical Properties of *Acacia auriculiformis* A. Cunningham Ex Benth Used As Timber in Benin, *Journal of Materials Science and Surface Engineering*, 8: 992-1000, ISSN (Online): 2348-8956. DOI: <https://doi.org/10.52687/2348-8956/815>.
26. Memento Du Forestier, 1981. Second revised and expanded edition, Paris (France), pp: 894.
27. Gerard, J., A.C. Kouassi, C. Daigremont, P. Detienne, D. Fouquet and M. Vernay, 1998. Synthesis on the technological reference characteristics of the main African commercial woods. CIRAD-forêt campus international de Baillarguet, Montpellier (France), pp: 189.
28. Kouchadé, A.C., K.S. Awokou, B. Kounouhéwa, D. Guibal, P. Langbour and J. Gérard, 2018. Determination of the physical and mechanical properties of *Anthonota fragrans* (Adonmoteu or Kibakoko) wood from Benin. *Afriques Science*, 14: 65-67. ISSN 1813-548X [www.afriquescience.info](http://www.afriquescience.info).
29. Tonouéwa, M., C. Gbémavo, C. Ouinsavi and N. Sokpon, 2013. Influence of climatic factors on the technological characteristics of the main timber and service woods in North-Benin, *Annals of the University of Parakou, Series "Natural Sciences and Agronomy"*, 2: 1-8.

30. Tonouéwa, J.F.M.F., P. Langbour, S.S.H. Biau, E.P.S. Assèdé, D. Guibal, C.A. Kouchadé and B.B. Kounouhéwa, 2020. Anatomical and physico-mechanical properties of *Acacia auriculiformis* wood in relation to age and soil in Benin, West Africa. *European Journal of Wood and Wood Products*, 78: 745-756. DOI: 10.1007/s00107-020-01540-x.
31. Hounlonon, M.C., A.C. Kouchadé and B.B. Kounouhéwa, 2017. Physical and mechanical properties of teak wood of Tanzanian and local provenance in Benin, Bois et Forêts des Tropiques, 331: 45-53.
32. Gérard, J., S. Paradis, D. Guibal, M. Vernay, J. Beauchêne, L. Brancheriau, I. Chalon, C. Daigremont, P. Détéienne, D. Fouquet, P. Langbour, S. Lotte, C. Méjean, M.F. Thévenon and A. Thibaut, 2011. *Tropix 7: The main technological characteristics of 245 tropical and temperate forest species*. CIRAD, Montpellier, France.
33. Sproßmann, R., M. Zauer and A. Wagenführ, 2017. Characterization of acoustic and mechanical properties of common tropical woods used in classical guitars. *Results Phys.*, 7: 1737-1742.
34. Ayarkwa, J. and F.W. Owusu, 2008. *Cylicodiscus gabunensis* Harms. In: Louppe D., Oteng-Amoako A.A. & Brink M., eds. *Prota 7(1): timbers/bois d'oeuvre 1*. Wageningen, The Netherlands: Prota.
35. Christoforo, A.L., T.H. Panzera, D.A.L. Silva, J. Fiorelli and F.A.R. Lahr, 2014. Shear and Longitudinal Modulus of Elasticity in Structural Lumber Beams, *International Journal of Materials Engineering*, 4: 31-36 DOI: 10.5923/j.ijme.20140401.04.
36. Longui, E.L., T. Yojo, D.R. Lombardi and E. S. Alves, 2010. The Potential of Ipê (*Handroanthus* spp.) and Maçaranduba (*Manilkara* spp.) Woods in the manufacture of bows for string instruments. *IAWA J.*, 31: 149-160.
37. Ribeiro, R.F.D.S., J.F.S. Feiteira, J.P. De Gouvêa and A.F. Ferreira, 2021. Experimental investigation on variability in properties of Amazonian wood species Muiracatiara (*Astronium lecointei*) and Maçaranduba (*Manilkara huberi*) focusing guitar fingerboards manufacturing. *Journal of Bioresources and Bioproducts*, 6: 33-38. <https://doi.org/10.1016/j.jobab.2021.02.006>.
38. DGEFC, 2019. *Compilation des annuaires statistiques et rapports annuels de la Direction Générale des Eaux, Forêts et Chasses (ex Direction Générale des Forêts et des Ressources Naturelles DGFRN)*.
39. Ekhuemelo, D.O., E.T. Tembe and M.T. Aondoaver, 2021. Assessment of physical and mechanical properties of three hardwood species from timber sheds in Makurdi, Benue state, Nigeria. *Proceedings of the 7th Biennial Conference of Forests and Forest Products Society, Held At University of Uyo, Uyo, Nigeria. 26<sup>th</sup>-30<sup>th</sup> April, 2021*.
40. Bello, A.A. and A.A. Jimoh, 2018. Some Physical and Mechanical Properties of African Birch (*Anogeissus leiocarpus*) Timber. *J. Appl. Sci. Environ. Manage.* January, 2018. 22: 79-84. DOI: <https://dx.doi.org/10.4314/jasem.v22i1.14>.
41. Hédin, L., 1929. Note on Adoum wood (*Cylicodiscus gabunensis* Harms). *J. Agric. Traditionnelle Bot. Appl.*, 95: 446-448.
42. Hidayat, W., J.H. Jang, S.H. Se-Hwi Park, F. Febrianto and N.H. Kim, 2007. Properties of Okan (*Cylicodiscus gabunensis*) Wood Thermally Modified at Different Temperatures, <math>\pm \mu\hat{I}\text{-B-07}>
43. Cloutier, A., 1992. Continuing education course presented to the Ordre des Ingénieurs Forestier du Québec, part I, update of the course n° 26. Université Laval Sainte-Foy (Québec) G1K 7P4, pp: 18.
44. Achim, A., M. Bernier and A. Cogliastro, 2009. Comparison of the mechanical properties of the wood of plantation with that of the natural forest: the case of the red oak. *Forest Resource Development Program - Component II. Project 16-2008-05*. Plant Biology Research Institute, pp: 18.
45. Richter, H.G. and M.J. Dallwitz, 2000 onwards. *Commercial timbers: descriptions, illustrations, identification and information retrieval*. In English, French, German, Portuguese and Spanish. Version: 9<sup>th</sup> April 2019. [deltaintkey.com/](http://deltaintkey.com/).
46. Keller, R. and C. Millier, 1970. Use of density components I n xylochronology. *Ann. Sci. Forest.*, 27: 157-196.
47. Wegst, U.G.K., 2006. Wood for sound. *Amer. J. Bot.*, 93: 1439-1448.
48. Konopka, D. and M. Kaliske, 2018. Transient multi-fickian hygromechanical analysis of wood. *Comput. Struct*, 197: 12-27.
49. Hernández, R.E. and G. Almeida, 2003. Effects of wood density and interlocked grain on the shear strength of three Amazonian tropical hardwoods. *Wood Fiber Sci.*, 35: 154-166.
50. Obataya, E., M. Norimoto and J. Gril, 1998. The effects of adsorbed water on dynamic mechanical properties of wood. *Polymer*, 14: 3059-3064.

51. Gerhards, C.C., 1982. Effect of moisture content and temperature on the mechanical properties of wood: an analysis of immediate effects. *Wood and Fiber*, 14: 4-36.
52. Hernández, E.R., L. Passarini and A. Koubaa, 2014. Effects of temperature and moisture content on selected wood mechanical properties involved in the chipping process. *Wood Sci. Technol.*, 48: 1281-1301. DOI 10.1007/s00226-014-0673-9.
53. FPL, Forest Products Laboratory, 2021. Wood handbook-wood as an engineering material. General Technical Report FPL-GTR-282. Madison, WI: U.S. Department of Agriculture, Forest Service, Forest Products Laboratory, pp: 543.
54. Ishimaru, Y., K. Oshima and I. Iida, 2001. Changes in the mechanical properties of wood during a period of moisture conditioning. *J. Wood Sci.*, 47: 254-261.
55. Brémaud, I. and J. Gril, 2020. Moisture content dependence of anisotropic vibrational properties of wood at quasi-equilibrium: analytical review and multi-trajectory experiments. *Holzforschung*. <https://doi.org/10.1515/hf-2020-0028>.