



CONSEIL AFRICAIN ET MALGACHE POUR L'ENSEIGNEMENT SUPÉRIEUR

01 BP 134 OUAGADOUGOU 01 (BURKINA FASO)
TEL (226) 25 36 81 46 - FAX (226) 25 36 85 73 - Email: comes@lecames.org

Article 11

Titre: Effects of Damp-Heat into Crystalline Silicon Photovoltaic Solar Modules in Benin (Tropical Area)

Auteurs : Minadohona Maxime Capo-Chichi, Vianou Irenée Madogni, Clément Adéyèmi Kouchadé, Géraud Florentin Hounkpatin, Basile Bruno Kounouhewa

Journal: Science Journal of Energy Engineering Volume 10, Numéro 2 , pp.24-34 (2022)

Lien :

<https://article.sciencepublishinggroup.com/pdf/10.11648.j.sjee.20221003.11.pdf>

Bases de données d'indexation : Chemical Abstracts (CAS Source Index - CASSI)

Nom : **KOUCHADE**

Prénoms : **Adéyèmi Clément**

Institution : Université d'Abomey-Calavi

CTS: Sciences et Techniques de l'Ingénieur




Tel: +229 94398889

email : ckouchade@yahoo.fr

Science Journal of Energy Engineering

[Home](#) | [Archive](#) | [Special Issues](#) | [Indexing](#) | [Editorial Board](#) | [Reviewers](#) | [Submission Guidelines](#) | [Article Processing Charges](#) | [Publication Ethics](#) | [Cop](#)

Archive

2022, Volume 10 
Vol. 10, Issue 4, Dec.
Vol. 10, Issue 3, Sep.
Vol. 10, Issue 2, Jun.
Vol. 10, Issue 1, Mar.
2021, Volume 9 
2020, Volume 8 
2019, Volume 7 
2018, Volume 6 
2017, Volume 5 
2016, Volume 4 
2015, Volume 3 
2014, Volume 2 
2013, Volume 1 

[Submit a Manuscript](#)

Special Issues

Published Special Issues
Propose a Special Issue
Special Issue Guidelines

[Join Editorial Board](#)

[Become a Reviewer](#)

[Home](#) / [Journals](#) / [Earth, Energy & Environment](#) / [Science Journal of Energy Engineering](#) / [Indexing](#)

Indexing

Science Journal of Energy Engineering has been included by the following Abstracting and Indexing databases:

Academickeys	Chemical Abstract Services
CNKI SCHOLAR	CrossRef
Directory of Research Journals Indexing	Eurasian Scientific Journal Index
EZB	MIAR
Polish Scholarly Bibliography	ResearchBib
Universal Impact Factor	Wissenschaftszentrum Berlin
WorldCat	Zeitschriftendatenbank

PUBLICATION SERVICES

[Journals](#)
[Special Issues](#)
[Conferences](#)
[Books](#)
[Copyright](#)

JOIN US

[Join as an Editor-in-Chief](#)
[Join as an Editorial Member](#)
[Become a Reviewer](#)
[Qualification & Requirement](#)
[Benefits & Responsibilities](#)

RESOURCES

[Open Access](#)
[For Authors](#)
[For Librarians](#)
[For Booksellers](#)
[Article Processing Charges](#)

SPECIAL SERVICES

[Download Certificates](#)
[Recommend to Library](#)
[Ordering from SciencePG](#)
[Subscribe](#)

ADDRESS

Science Pul
 1 Rockefeller
 10th and 11
 New York, N
 U.S.A.
 Tel: (001)34

CAS Source Index (CASSI) Search ResultDisplaying Record for Publication: [Science Journal of Energy Engineering](#)

Entry Type	Active Serial
Title	Science Journal of Energy Engineering
Abbreviated Title	Sci. J. Energy Eng.
CODEN	SJEEAN
ISSN	2376-8126
Language of Text	English
Summaries In	English
History	v1 n1 Apr. 2013+
Publication Notes	Avail. from Internet at URL: http://www.sciencepublishinggroup.com/journal/archive.aspx?journalid=269&issueid=-1
Publisher Name	Science Publishing Group

Disclaimer

Effects of Damp-Heat into Crystalline Silicon Photovoltaic Solar Modules in Benin (Tropical Area)

Minadohona Maxime Capo-Chichi*, Vianou Irenée Madogni, Clément Adéyèmi Kouchadé, Géraud Florentin Hounkpatin, Basile Bruno Kounouhewa

Laboratory of Radiation Physics, Faculty of Science and Technology, University of Abomey-Calavi, Cotonou, Benin

Email address:

cachi1550@gmail.com (Minadohona Maxime Capo-Chichi), madognimadogni@gmail.com (Vianou Irenée Madogni), ckouchade@yahoo.fr (Clément Adéyèmi Kouchadé), hounkpatinrd23@gmail.com (Géraud Florentin Hounkpatin), kbbasile@gmail.com (Basile Bruno Kounouhewa)

*Corresponding author

To cite this article:

Minadohona Maxime Capo-Chichi, Vianou Irenée Madogni, Clément Adéyèmi Kouchadé, Géraud Florentin Hounkpatin, Basile Bruno Kounouhewa. Effects of Damp-Heat into Crystalline Silicon Photovoltaic Solar Modules in Benin (Tropical Area). *Science Journal of Energy Engineering*. Vol. 10, No. 2, 2022, pp. 24-34. doi: 10.11648/j.sjee.20221003.11

Received: July 24, 2020; **Accepted:** August 10, 2020; **Published:** November 10, 2022

Abstract: During their outdoor service, photovoltaic (PV) modules are exposed to different set of environmental conditions that can affect their performance such as Damp-Heat. But these external conditions varied from one area to another. This work aims to highlight the impact of environmental conditions on the performance of crystalline silicon photovoltaic solar modules exposed in the tropical environment which is a hot and humid area. We have firstly studied the degradation of the solar photovoltaic module under the effect of moisture and the heat by using the analytical models of Eyring, Peck and Laplace transformed. Then we have compared these models to the experimental Damp Heat model of Hulkoff. We finally verified the impact of the environmental conditions of the tropical environment on the photovoltaic modules by simulating their behavior over time under real conditions using the relative humidity and average temperature data of the synoptic stations of Benin. The theoretical results obtained, compared to those obtained by Hulkoff in experiments showed firstly a reduction of about 3% in the electrical performance of photovoltaic solar modules over period and a loss of performance of PV modules ranging from 0.19% to 0.5% per year. The PV module performance degradation rates over the study period correlate with those found in the literature on different systems installed in various regions of the world. So, future researches on crystalline silicon photovoltaic solar module can be effect of Damp-Heat on its electrical parameters in tropical area.

Keywords: Environmental Conditions, Performance, Module, Damp-Heat, Electrical Power

1. Introduction

Photovoltaic solar technology has been considered for many years as a future solution to supplement conventional energy sources that were previously used in the world. Therefore many laboratories are engaged in the manufacture of the base material which is silicon while working for the improvement of its yield. Thus, several types of cells are used today in the manufacture of solar panels, namely mono-crystalline cells, poly-crystalline cells, amorphous cells, organic cells and very recently perovskite. The performance of these cells is strongly influenced by climatic conditions when exposed to long term [1]. Moisture could be one of the factors affecting the efficiency of these cells, which reduces their

electrical performance. In fact, the absorption of the moisture leads to a darkening of the glass in its lower part in contact with the encapsulation material thus causing corrosion [2] and more particularly that of metallization [3]. Moreover, the penetration of moisture into the encapsulant can cause the reduction of light transmission [4]. Moisture also tends to increase the electrical conductivity of the coating material and therefore increases the leakage current thus impairing performance. Also, it may be the cause of the delamination of the module which, in turn, increases the temperature of the affected sites and accelerates the degradation process [3].

Several degradation tests have been used to monitor the degradation of the performance of exposed cells in outdoor conditions in various regions. This work was carried out

according to the following chronology: in Part 1, through a brief state of the art, we described the operating principle of the cell in question and gives an update on the effects of moisture and heat on the cells (the case of relative humidity), then in Part 2 the results obtained and the discussion were presented and finally in Part 3, the conclusion, perspectives and recommendations were made.

2. Material and Methods

2.1. Visual Degradation

In the literature, several authors had worked on the effect of the ingress of moisture into the solar panel in different climatic areas. They used various processes to study that phenomenon. Some of them used the laboratories tests as accelerated test and others observed the solar panel which was exposed for environmental stresses for several years. They noticed that moisture can enter into the solar panel in several ways. Thus:

- 1) Moisture can penetrate inside the solar panel through the Backsheet or the edges. It so tends to increase the electrical conductivity of the embedding material and therefore increases the leakage current thus implying degradation of performance [3]. Otherwise the intrusion of moisture can also be the cause of delamination of the module which in turn, increases the temperature of the affected sites and corrodes cell metallization in crystalline silicon panels [3].
- 2) It can also enter the panel through the rolled edges causes corrosion [8]. Moisture retention in the panel housing increases the electrical conductivity of the material. Indeed, corrosion attacks the metal connections of photovoltaic cells causing a loss of performance by increasing the leakage currents. Corrosion also degrades the adhesion between the cells and the metal frame (Figure 1b). In the same way, Skoczek and the co-workers [9] showed that moisture penetration into the

panel resulted in various chemical and physical degradations such as metallic corrosion of the module structure (Figure 1c). The resulting delamination phenomenon is more common in hot and humid climates.

- 3) Mekhilef and the co-workers found that when photovoltaic cells are exposed to moisture for the long term, there is some degradation in their performance. The high content of water vapor in the air causes delamination of the encapsulant. The water droplets trapped inside the wall serve as an optical screen for the cells thus reducing their performance (Figure 2a, 2b) [10]. Moisture ingress into the module reduced adhesion strength that can cause delamination of PV modules [4] (figure 2b).
- 4) Moisture penetrates mainly from the open edges when the impervious back material is used while moisture can diffuse both from the backsheet and the edges, when the permeable back material is used. In addition to diffusion, moisture can also enter the modules through capillary cracks or delaminated areas, in which case permeability can be very important. In addition, penetration of moisture into the encapsulant can cause the reduction of light transmission (Figure 3).

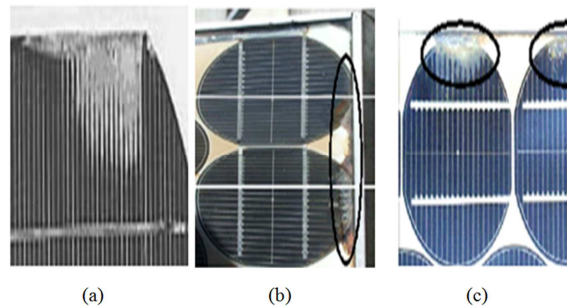


Figure 1. Effect on Moisture ingress [3, 8, 9].

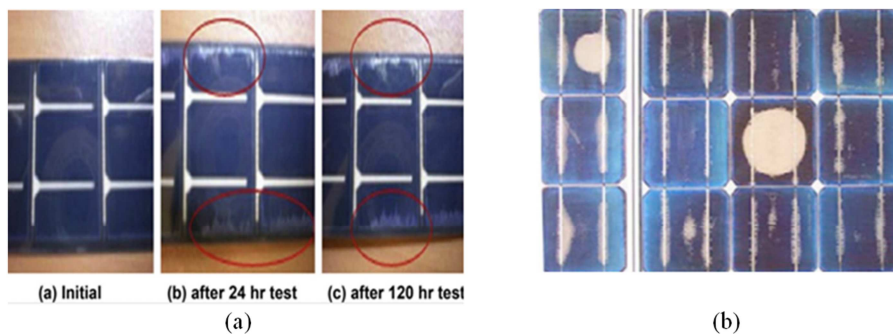


Figure 2. Delamination of the encapsulant by the entry of moisture [10].

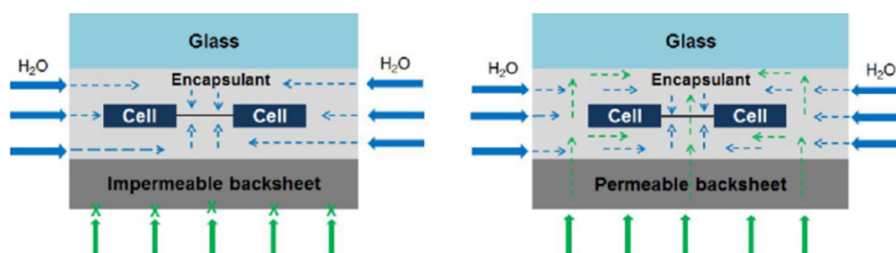


Figure 3. Moisture ingress into PV modules [4].

We can conclude that moisture ingress into PV module has some effects on its electrical performance. In the following part, we study those effects and their consequences on the lifetime of the module in our environment.

2.2. Humidity Induced-degradation

The lifetime of a PV module can be defined as a point in time when the module is no longer acceptable for any reason, or when the output power has fallen below a minimum acceptable value [11]. For the users, it is difficult to know exactly when their module will lose its electrical performance though the manufacturer indicated his lifetime. We must also say that the module's lifetime depends on the environmental conditions in which it is used. Moisture, one of these conditions has many effects on the degradation of the various materials constituting the module. Figure 4 illustrates the different ways through which moisture ingresses the module.

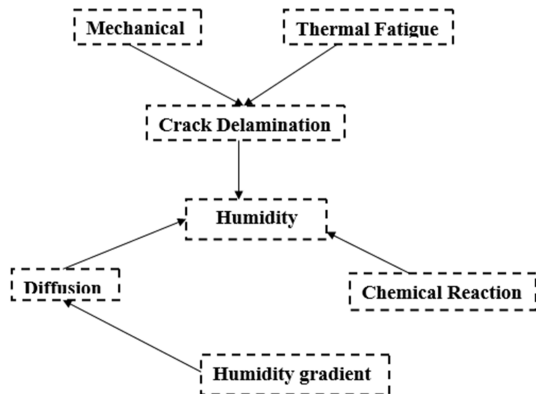


Figure 4. Different ways of moisture ingress in the module [12].

Figure 5 reveals the effects of humidity on the various module materials and the mechanisms those induced degradation.

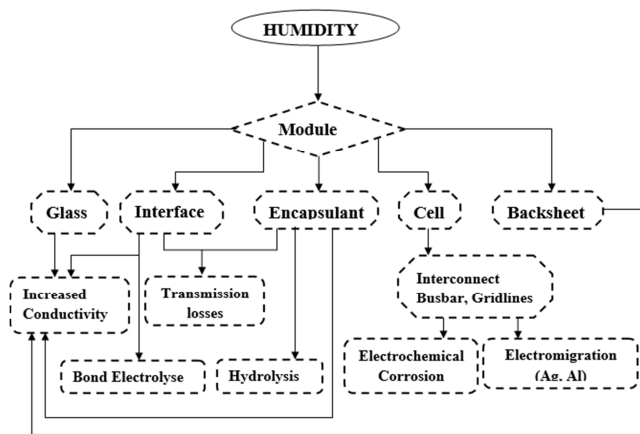


Figure 5. Effects of moisture and degradation mechanism [12].

The encapsulant material degradation induced by humidity ingress causes a loss of electrical performance of the module. Like shown in Figure 6, the effect of humidity on the encapsulant material is very important.

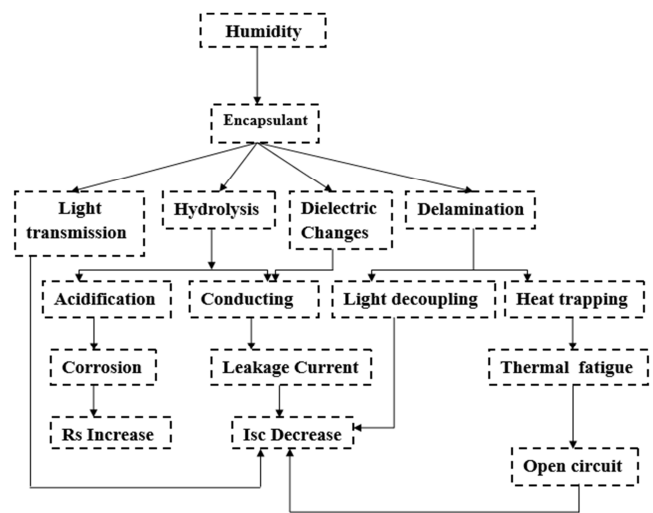


Figure 6. Degradation mechanisms of PV module encapsulant-Impact on module performance [12].

2.3. Thermally-induced Degradation

The temperature of cells/modules is usually higher than ambient temperature. Moreover, thermal effect acts as an accelerating factor for degradations caused by humidity or irradiance. Thermal cycles can reduce module reliability in a number of ways. For glass, residual strains may exist after lamination which can result in breakage or delamination between glass/polymer under thermal strains. For encapsulant, different photo-thermal and thermal reactions can happen together with UV radiation from light. The principal reactions of EVA are what are called Norrish I and Norrish II. In Norrish I, the vinyl acetate group can take off from the main chain to form acetaldehyde together with some gases which have the potential to further lead to bubbles in the module. In Norrish II, C=C bonds (polyenes) are formed which have been widely considered as the chromophore group for EVA discoloration. Besides that, acetic acid is produced to catalyze discoloration and corrosion reaction.

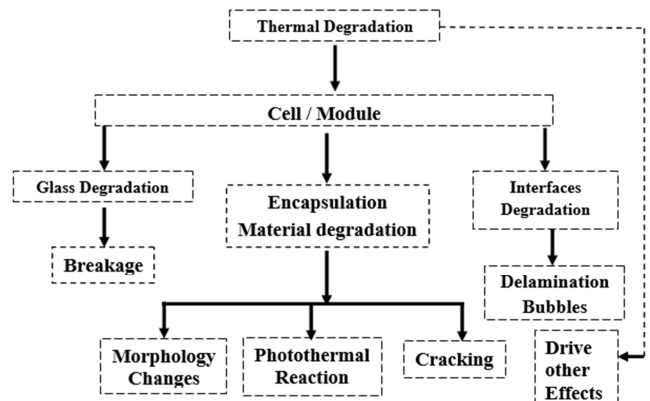


Figure 7. Effects of temperature and degradation mechanism [12].

The polyenes produced in Norrish II can further be oxidized to form α - β unsaturated carbonyl, another product leading to discoloration [13-15]. Besides chemical reactions, polymer may also undergo morphology changes under high

temperature. Cells can also suffer from thermal fatigue with reported cracking and solder joint degradation. With regards to interfaces, the thermal heterogeneity of different materials can induce cracks, bubbles and delamination under daily thermal cycles. Besides these direct defects, temperature can accelerate many degradation processes. The water diffusion through polymers has been reported to be accelerated by temperature in the Arrhenius form [16]. Other procedures like metallization corrosion, leakage current, diffusion of dopants, impurities, occur more rapidly at higher temperature.

2.4. Damp-Heat Exposure

During the aging, several types of visual defects have been observed. Some more severe are represented in (Figure 8). Delamination was observed, mainly in the corners and edges of the module. The absence of edge seal in the module has made the edge directly open to the environment where stronger influences were observed compared to the areas with a barrier effective against moisture. The penetration of moisture into the module was also observed and bubbles appeared at the glass/EVA interface. After 24 hours aging at 95°C/85% RH, a large bubble around the electrodes was observed. This is due to the bad protection around the external contacts where an access opening in the backsheet is not well sealed, allowing so the entry of water vapor.

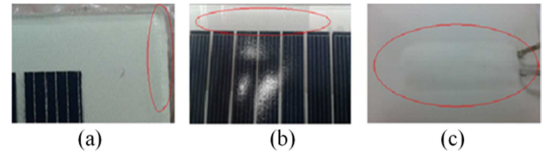


Figure 8. Defaults observed after a Damp-heat test: (a): edge/corner separation; (b): moisture entry and (C): bubble near the electrode exit.

The bubbles are usually due to chemical reactions that emit trapped gases in the cell/PV module. The bubbles located on the front side of the module produce a reduction in the radiation that arrives on the module. This causes decoupling of light and increases reflection [17]. This type of defect is similar to delamination. These defects appear in the center of the cell and may be due to poor cell adhesion due to high temperature [17, 18]. When the gas forms at the back of the PV module, a mass appears in the encapsulant or in the back sheet, forming a bubble. Bubbles make the heat dissipation of cells more difficult, overheating and reducing thereafter the lifetime of these cells.

2.5. Affected Parameters

Degradation factors affect many parameters in photovoltaic modules. Some of these affected parameters, the degradation modes, the affected materials as well as the degradation factors are recorded in the table below.

Table 1. Affected parameters.

Degradation categories	Degradation Behaviours	Influenced Materials	Contributing stress
Isc Losses	Light scattering by water	Interfaces and bulk encapsulant	Moisture, temperature, May drive, Moisture ingress
	Increased light absorption	Pottant	Moisture, thermal
	Encapsulant Discoloration	Pottant	Irradiance, thermal
	Light transmission decoupling due to cracks, delamination and bubbles	Glass, cell, interfaces	Thermal, Fatigue, moisture
	Light induced degradation	Cell	irradiance
R _s increase	Diffusion of dopants/impurities causing recombination	cell	Voltage, thermal
	Front/back Contact/Interconnect/lead corrosion	Metal components	Moisture, Voltage, Temperature May accelerate
	Solder joint crack	Solder joint	thermal
	Metal electro migration/diffusion	Metal component	Voltage, Temperature, May accelerate
R _{sh} reduction	Leakage current	semiconductor	Voltage, thermal
	Encapsulant dielectric damage	Interface, Pottant, Glass surface	Voltage, Moisture
	Cell junction Conductivity increase	Encapsulant semiconductor	Moisture Voltage

The influence of degradation on the above-mentioned parameters induces degradation rates which vary from one environment to another as shown in Table 2.

Table 2. Degradation rates obtained in the literature.

Authors	R _D per year	Years
king and al.	0.5%	2000 [24]
Quintana MA and al.	0.5%	2000 Utah (USA) [25]
Realini A.	0.2% on 20 years	2001 and 2003 (Swiss) [26, 27]
Reis and al.	0.4% on 11 years	2002 Arcata (USA) [28]
Sakamoto and al.	< 0.5%	2003 Osaka (Japan) [29]
Hedström J. and al.	0.17% on 30 years	2006 Sweden [30]
Saleh IM and al.	1% on 11 years	2009 Lybia [31]
Vignola F. and al.	Behind 0.6 and 1.5%	2009 Oregon (USA) [32]
Eikelboom JA. and al.	0.3% on 2 years	2000 [33]
Juan Lopez-Garcia	0.24% on 20 years	2017 (Luxembourg) [34]

2.6. Principle of Operation of the NTS5E3E Panels

The study was based on a mono crystalline silicon (inorganic cell) panels having as a band diagram the one represented in Figure 9. Its operation is based on the principle of converting the photon flux into electrical energy through the following mechanisms [5, 6]:

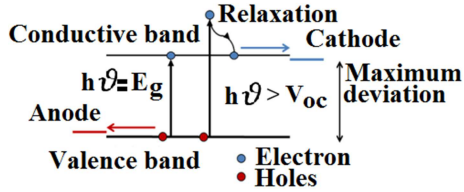


Figure 9. Band diagram and operating principle of the cell [6].

- 1) Absorption of incident photons by the active material constituting the cell;
- 2) Creation of electron-hole pairs in the semiconductor material;
- 3) Collection of the carriers generated in the device.

E_g : Minimum energy for possible photon absorption when $h\nu > E_g$, the extra energy is lost to thermodynamic expansion [5, 7].

The absorption of a photon by the photoactive semiconductor is related to the energy of the band gap of the semiconductor. The photon of sufficient energy excites an electron from the valence band to pull it out of the material and pass it to the conduction band. The electron leaving the valence band leaves a positively charged hole in this band. The electron-hole doublet is then extracted by the external circuit generating a current whose power conversion efficiency is defined as [6]:

$$\eta = \frac{J_{sc} \times V_{oc}}{P_i} \times FF \times 100\% \quad (1)$$

With:

P_i : incident light power in W/m^2 ; J_{sc} : short-circuit current density in A/cm^2 ; V_{oc} : open circuit voltage, FF : fill factor.

2.7. Analytical Models

2.7.1. Eyring's and Peck's Models

Moisture in a PV module is a degrading factor that affects the performance of the PV cell. But when this humidity penetrates the PV module, it affects differently the front and the backside of encapsulant. In a PV module, humidity is assumed to be constant when exposed to certain damp heat conditions. We used the Eyring's and Peck's models to analytically simulate the entry of moisture into the module as a function of the humidity on the backside of the module at constant temperature and then as a function of temperature at constant humidity [19].

$$rh_{eff,Eyring} = (a - b \times T) \times \frac{c \times rh_{back} + d}{e} \quad (2)$$

$$rh_{eff,Peck} = (a' - b' \times T) \times \frac{c' \times rh_{back} + d'}{e'} \quad (3)$$

Where a, b, c, d, e, a', c', d', e' are models parameters; T: ambient temperature; rh_{back} : humidity of the backside encapsulant.

Escobar and Meeker [20] in their work and Park [19], proposed two degradation models: Eyring's and Peck's models, commonly used when the stress conditions are temperature and humidity (acceleration constraints during Damp Heat tests). Formulas 3 and 4 as follows give the expressions of the degradation rates of the PV cells:

$$R_{D,Eyring} = A \times \exp\left(\frac{-E_a}{k \times T} - \frac{\alpha}{rh_{eff,Eyring}}\right) \quad (4)$$

$$R_{D,Peck} = B \times \exp\left(\frac{-E_a}{k \times T}\right) \times (rh_{eff,Peck})^n \quad (5)$$

Where E_a : thermal activation energy of the degradation process (eV), k : Boltzmann constant (8.62×10^{-5} eV/K), T : temperature (K), and rh : relative humidity (%). A and b : two constants dependent on the failure mode.

When the degradation rates are obtained, the expression of the average power given by [2] has been used to give the evolution of the mean power of the module as a function of time according to the two models. This expression is as follows:

$$P_{mean,t} = P_{max,0} \times (1 - R_D)^t \quad (6)$$

We also determined from these two models the evolution in time of the form factor of the studied PV module by using the following expression:

$$FF = \frac{P_{mean,t}}{V_{oc} \times j_{sc}} \quad (7)$$

Where:

V_{oc} : Open circuit voltage and j_{sc} : short circuit current.

2.7.2. Laplace Transformed

In this part we have used the results of the damp heat test (DH: damp heat) carried out in controlled atmosphere climatic chambers. The experimental results obtained by Hulkoff in 2009, we determined the law of evolution of the power output of the "Sharp NTS5E3E" module with mono crystalline silicon. From Laplace transform, we found the power transfer function using the evolution law obtained from experimental tests. The transfer function thus found was introduced into the model.

The equation of the linear trend curve of the power obtained experimentally by Hulkoff is given by:

$$P_{max} = at + b \text{ with } a = -21.56175 \text{ and } b = 185 \quad (8)$$

The general expression of the transfer function in the Laplace domain is written:

$$S(p) = \int_0^{\infty} f(t) \exp(-pt) dt \quad (9)$$

The expression of the transfer function of the maximum output power is given by:

$$G_{P_{max}}(p) = \frac{185p - 21.56175}{p} \quad (10)$$

The variation of the maximum output power of the module obtained with respect to the number of years of degradation is given as follows:

$$P_{max}(t) = -0.11655t + 185 \quad (11)$$

3. Results and Discussions

Figures 10 and 11 show the effect of the effective humidity in the module at constant temperature on the one hand and at constant humidity on the other. For that, we chose to use exclusively the model of Peck which is a model of humidity (eq. 3). First, the temperature is kept constant and the humidity varies and then the humidity is kept constant and the temperature varies. When the temperature is kept constant, the effective humidity increases, but when it is the humidity that is kept constant, the effective humidity decreases.

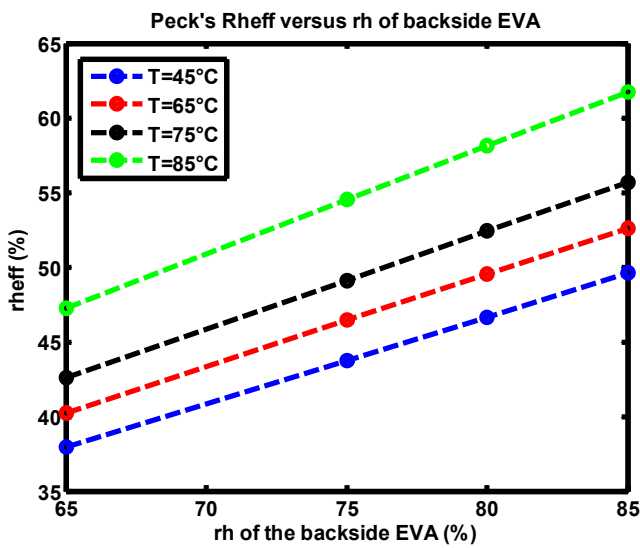


Figure 10. Rheff versus rhback at constant temperature.

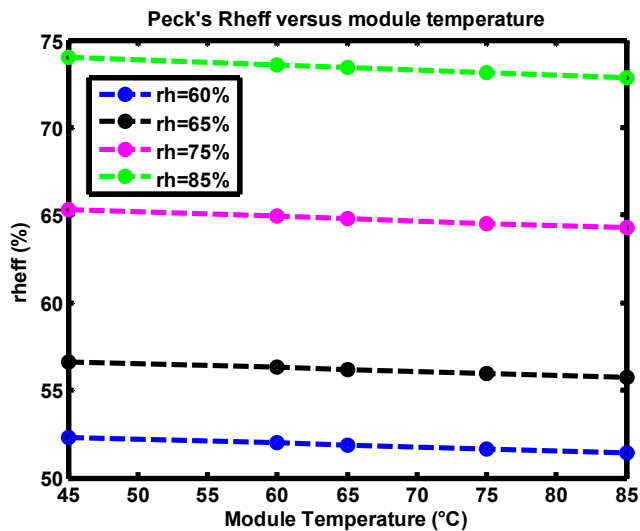


Figure 11. Rheff versus module temperature at constant humidity.

With the Eyring model, when the humidity varies keeping the temperature constant, there is a higher loss of performance.

When the temperature varies with constant humidity, there is less loss of performance at the cell level (Figure 12). The Eyring's model is more sensitive to humidity variation when temperature is constant than when temperature varies by keeping the humidity constant.

With the Peck model, when the humidity varies keeping the temperature constant, there is less loss of performance. When the temperature varies with constant humidity, there is more loss of performance in the cells (Figure 14).

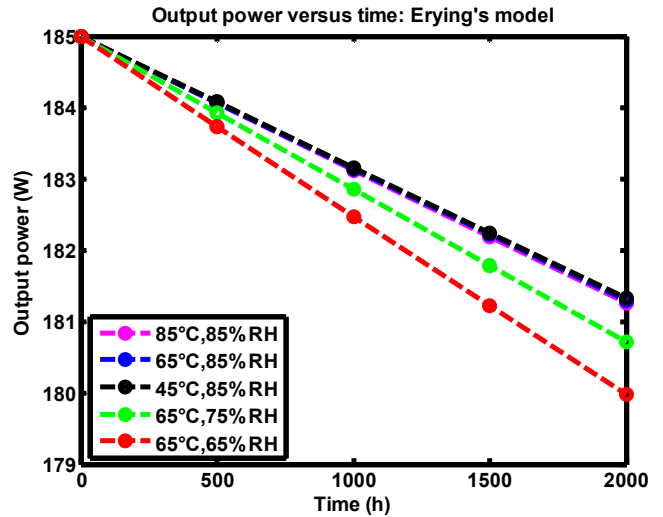


Figure 12. Output power according to time.

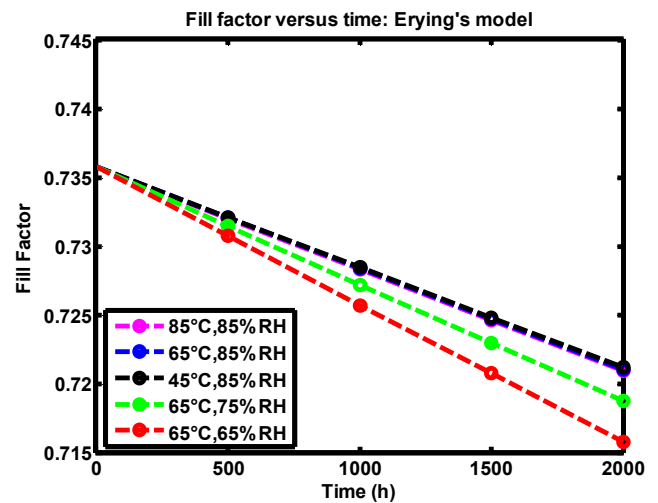


Figure 13. Fill Factor according to time.

The Eyring's model is more sensitive to humidity variation when temperature is constant than when temperature varies by keeping the humidity constant. The Peck model is more sensitive to temperature variation when humidity is constant than when humidity varies by keeping the temperature constant.

The two models complement one another because Eyring's is sensitive to humidity variation and Peck's is sensitive to temperature variation. The same results were obtained for the fill factor (Figures 13 and 15).

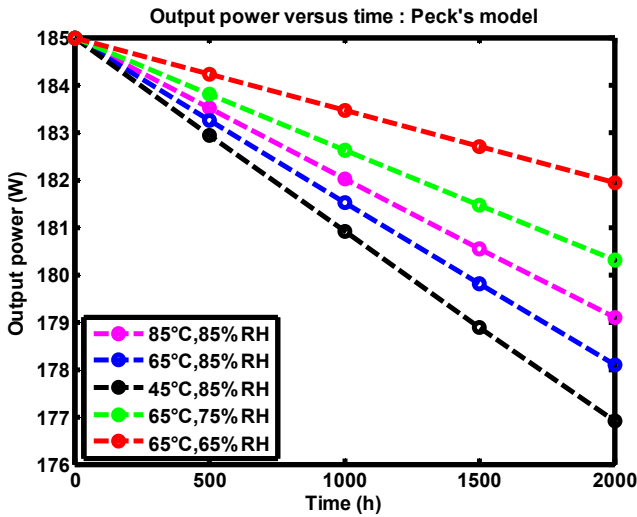


Figure 14. Output power according to time.

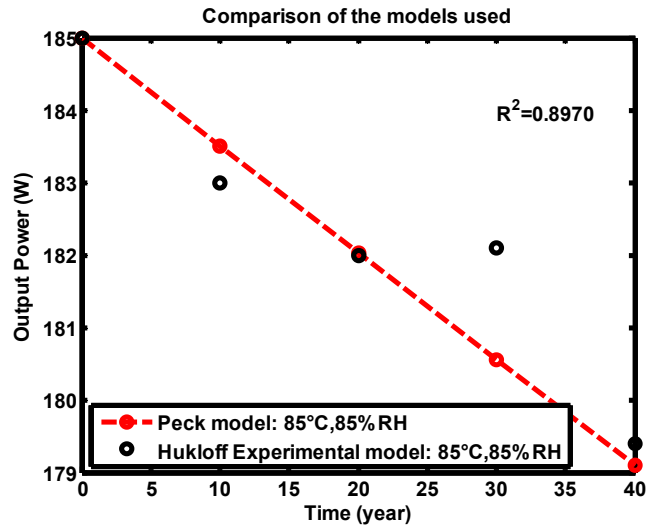


Figure 16. Output power according to time (Peck and Hukloff models).

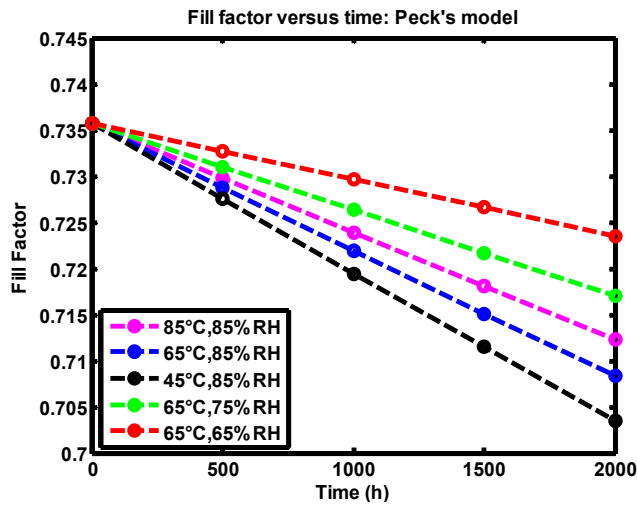


Figure 15. Fill Factor according to time.

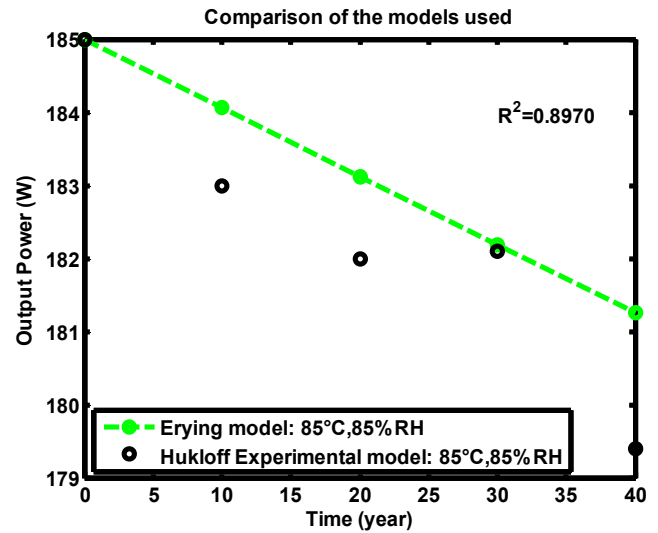


Figure 17. Output power according to time (Erying and Hukloff models).

3.1. Validation of the Analytically Models Used

The lifetime of PV cells is estimated at 20 years, according to several manufacturers. To find out the degradation mechanism, the cells are subjected to accelerated degradation tests in the laboratory. One of the tests of degradation carried out, the best known is that realized by Hukloff in 2009 in Miami in Florida State. The tests are carried out in a controlled atmosphere in climatic chambers under 85°C/85% RH for 1000 hours corresponding to 20 years in real conditions. These tests recommend not exceeding 5% degradation of the performance of the module. But in 1000 hours, this rate is not likely to be reached so it is recommended to extend up to 2000 hours corresponding to 40 years in real conditions. The analytical models were simulated over a period of 20 years and then 40 years. To validate the analytical models used by Hukloff experimental model, we compared the times in laboratory and real conditions.

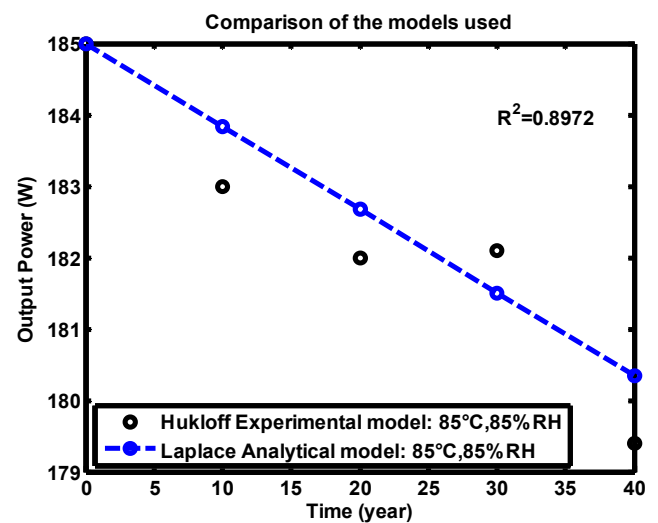


Figure 18. Output power according to time (Laplace and Hukloff models).

Figure 19 shows the comparison between the two models, the Laplace transform and the Hukloff experimental model.

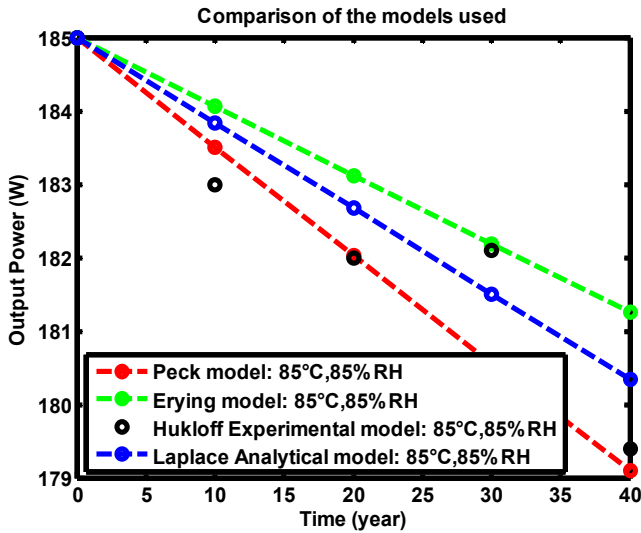


Figure 19. Output power according to time (The four models).

The variations of the degradation rate for the used models are given in the table 3 as follows:

Table 3. Performance loss during 40 years.

Models	Performance loss During 40 years	Study
Peck	2.76%	This study
Eyring	2.02%	This study

Models	Performance loss During 40 years	Study
Laplace	2.52%	This study
Laplace	2.70%	Radhia DOUMANE and al. 2013 [2]
Hulkoff	2.30%	Hulkoff, 2009 [36]

We have observed a better correlation between Hulkoff's experimental model and analytical modeling results.

3.2. Peck's Model Applied in the Tropical Area (Benin)

3.2.1. Site Description

The tropical humid area is the largest climatic group on the surface of the globe and the only one in a single unit, since it extends approximately symmetrically on both sides of the equator. This area is defined as the part of the earth's surface that twice a year, receives perpendicularly at midday the rays of the sun when it goes to the zenith. This zone is around the equator, from 23.5 degrees north latitude to 23.5 degrees south latitude and extends in total to 46°55' of latitude, symmetrically on both sides of the equator. Throughout the year, therefore, and over the entire extension of the tropical zone (Figure 20), the sun rises every day high in the sky: there is no real winter. The tropical zone is a hot and very rainy zone and the winds are laden with humidity. The persistent combination of heat and humidity can be the cause of the degradation of crystalline silicon PV cells [21].

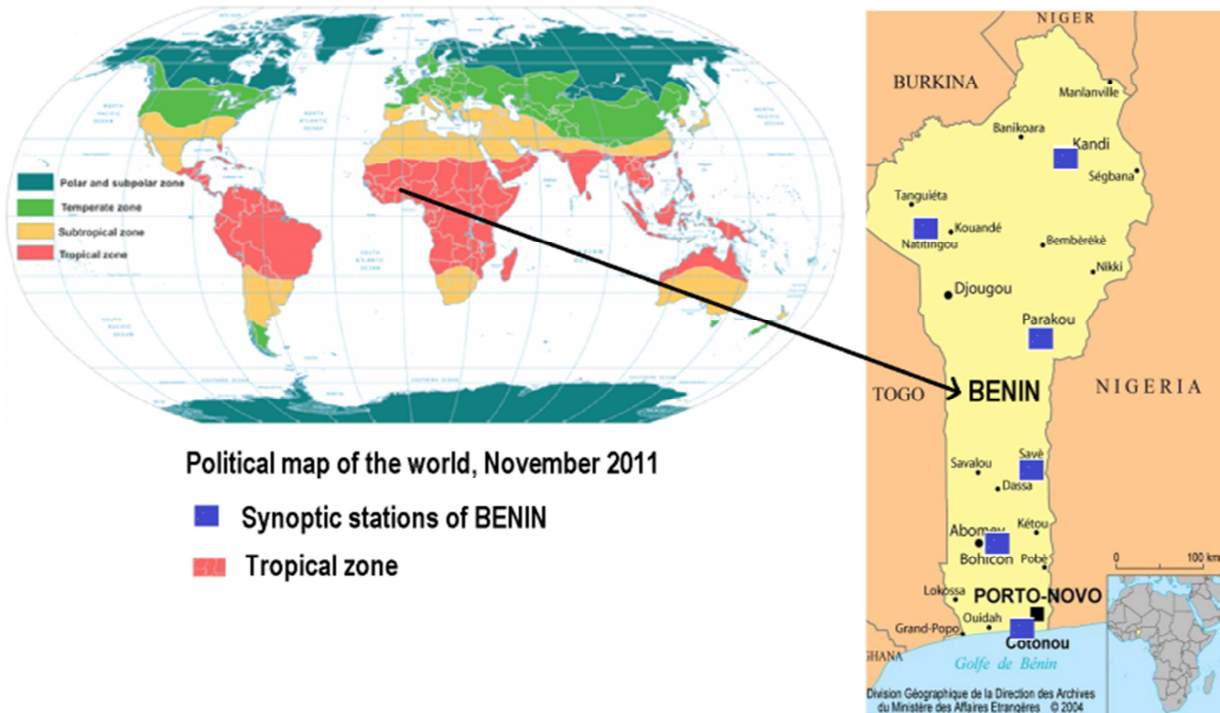


Figure 20. Geographic location of Tropical Zone and the synoptic stations of BENIN (Source: political map of the world, November 2011).

3.2.2. Modeling of PV Modules Degradation in the Tropical Area

The tropical area is characterized by high humidity (70 to 90% RH) [22] and a high temperature up to 45°C in real conditions. Eyring's and Peck's models can therefore be used

to simulate the degradation over time of crystalline silicon PV modules.

We used the data of temperature and relative humidity of synoptic stations of Benin (Figure 20) over a period of 40 years (1967 to 2007) to evaluate the degradation rates of the PV modules.

Benin is located between latitudes 6° and 12°30 N and longitudes 1° and 4°E, presents at south a subequatorial climate with two rainy seasons and two dry season. At north the climate is Sudanese with a moist season and a dry season. At south the average annual pluviometric decreases from Porto-Novo (1200 mm) to Grand-Popo (820 mm). The average monthly temperature varies from 20°C to 34°C. At north the temperatures are high, and the rainfalls are weaker between 890 and 700 mm except on the which receives on average 1300 mm in Natitingou [23].

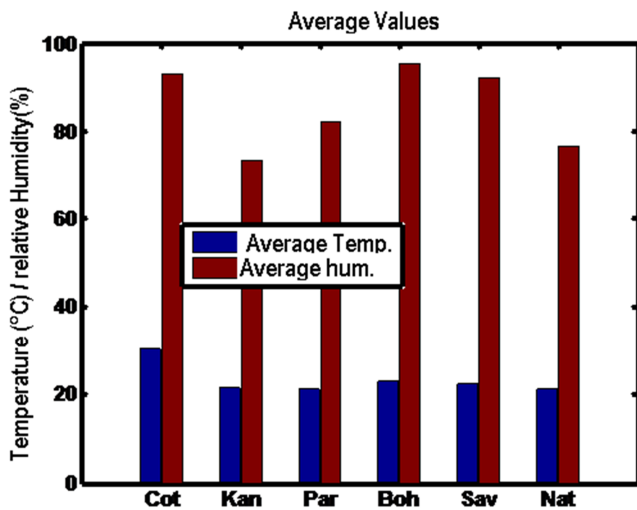


Figure 21. Average interannual temperature and relative humidity.

Figure 21, showed average interannual temperature and relative humidity values of synoptic stations in Benin.

Table 4. Degradation rates in the six synoptic stations of Benin (Figure 20).

Cities	Cotonou	Kandi	Parakou	Bohicon	Savè	Natitingou
R _D (40 years)	12.02%	7.76%	9.95%	13.03%	19.64%	14.07%
R _D (per year)	0.3%	0.19%	0.25%	0.33%	0.5%	0.35%

These degradation rates obtained in the six cities of Benin were compared with those found in the literature (Table 2).

The results found to compare with those obtained in this work show that the results are similar and that the model used is appropriate.

4. Conclusion

We have from the experimental Damp-Heat data of Hulkoff (2009), validated the Eyring and Peck analytical models. The results obtained compared with those obtained in the literature are consistent. The power degradation rates obtained are less than 5% as recommended by the International Electro technical Commission [2]. The Peck model was used to calculate, over a period of 40 years, in different cities of Benin, the degradation rate of the PV module NTS5E3E with peak power 185 Wc. The results obtained showed degradation rates of between 0.19% and 0.5%/year. This rate varies from one city to another. But the results obtained are consistent with those found in the literature (Table 4) where for crystalline silicon the rate is around 0.5%/year. Degradation rates of less than 0.5%/year are required to meet long-term guarantees. The peck model that is

used when the damage mechanism is sensitive to humidity and temperature allows determining in real time and in real conditions, the degradation rate of the electrical power.

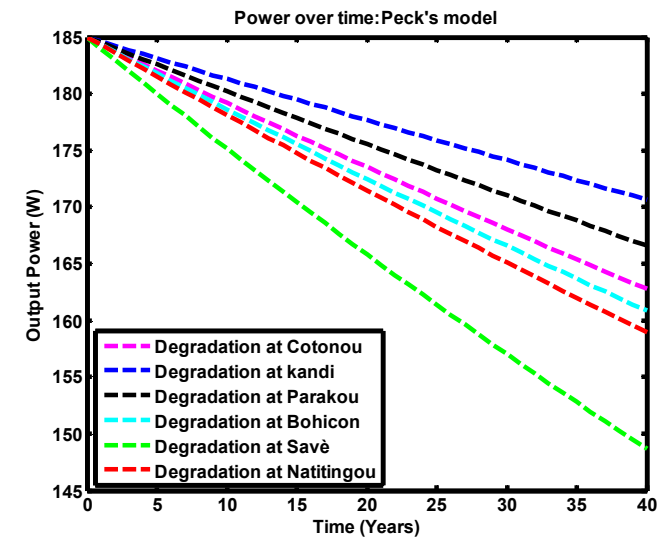


Figure 22. Interannual degradation of power Electric: 1967 to 2007.

The annual electrical power degradation rates of the NTS5E3E module in the six cities of Benin are calculated and summarized in the following table.

The highest rate (0.5%/year) was obtained at Savè in the center of the country which is a hilly region and therefore an area of excessive heat from the reflexivity of the hills and the fact that the atmospheric humidity coastline (monsoon flow) is trapped by the latter. This reveals that the high atmospheric humidity and temperature have an important effect on the degradation of the modules. A similar result was recently found by Park, who after doing an accelerated Damp-Heat test on three types of modules with different encapsulant (PVB, olefin and EVA) realized that after 1000h of test corresponding to 20 years in real conditions, PV modules encapsulated with EVA and olefin exhibiting a degradation rate of approximately 0.5%, a rate lower than that necessary to meet reliability or stability requirements. So modules encapsulated with EVA and olefin are more suitable for environments where environmental conditions (Humidity and temperature) are more severe such as in the tropics [37]. The utility of the Damp-Heat test is confirmed by Hyun-A Kim who believes that Damp Heat test is the degradation test of PV

modules in harsh environments like tropical area [38]. Further research is thus needed on PV to perform the profile effect of Damp-Heat on the electrical parameters into crystalline silicon photovoltaic solar modules in tropical area.

Competing Interests

Authors have declared that no competing interests exist.

Acknowledgements

Authors wish to acknowledge Odjouchi Raoufou YESSOUFOU, Guy Hervé HOUNGUE and H. E. Venance DONNOU for useful advice and suggestions.

References

- [1] Boussaid M., (2012). Modélisation des phénomènes de vieillissement des modules photovoltaïques. Mémoire de Magister, Université Abou-Bakr Belkaïd-Tlemcen.
- [2] Doumane R. (2011), Modélisation du vieillissement du module photovoltaïque, Mémoire de Magister, Université M'hamed BOUGARA, Boumerdes.
- [3] Quintana M. A. et al., (2002). Commonly observed degradation in field-aged photovoltaic modules. In: Proc. 29th IEEE Photovoltaic Specialists Conference, pp. 1436–1439.
- [4] Wu D. (2015). Investigation of the Reliability of the Encapsulation System of Photovoltaic Modules», Thèse de doctorat, Loughborough University.
- [5] Madogni V. I. (2016). Modèle analytique pour l'étude de la dégradation de la performance des cellules photovoltaïques au silicium monocristallin. Afrique SCIENCE, 12 (3): 182-200, 19 pages.
- [6] Thuillier B. (2001). Caractérisation structurale des contacts ohmiques réalisés à partir d'encres métalliques sur cellules photovoltaïques en silicium multi cristallin. Thèse de doctorat, Ecole Doctorale Matériaux de Lyon, l'institut national des sciences appliquées de Lyon, Lyon.
- [7] Nyman M. (2015). Interfacial Effects in Organic Solar Cells, Thèse de Doctorat, Abo Akademi University, Finland.
- [8] Kempe, M. D. (2005.). Control of moisture ingress into photovoltaic modules. In: 31st IEEE Photovoltaic Specialists Conference and Exhibition, Lake Buena Vista, Florida.
- [9] Skocze, A., Sample T., Dunlop E. D., Ossenbrink, H. A., (2008). Electrical performance results from physical stress testing of commercial PV modules to the IEC61215 test sequence». Solar Energy Materials and Solar Cells 92, pp 1593–1604.
- [10] Mekhilef S., Saidur R., Kamalisarvestani M. (2012). Effect of dust, humidity and air velocity on efficiency of photovoltaic cells, Renewable and Sustainable Energy Reviews 16, pp 2920– 2925.
- [11] Osterwald C. R. and McMahon T. J., (2009). History of Accelerated and Qualification Testing of Terrestrial Photovoltaic Modules: A Literature Review. Prog. Photovoltaic: Res. Appl. 2009; 17: pp 11–33.
- [12] WU D. et al., (2012). PV module degradation mechanisms under different environmental stress factors. IN: Hutchins, M., Pearsall, N. and Cole, A. (eds.) Proceedings of the 8th Photovoltaic Science Application and Technology Conference (PVSAT-8), Northumbria University, Newcastle upon Tyne, pp. 177 - 180.
- [13] Kurtz S., Whitfield K., Tamizhmani G., Koehl M., Miller D., Joyce J., Wohlgemuth J., Bosco N., Kempe M., Zgonena T. (2011). Evaluation of high-temperature exposure of photovoltaic modules. Progress in Photovoltaics: Research and Applications, 12, pp 954-965.
- [14] Park S., Dhakal R., Lehman L., and Cotts E., Measurement of deformations in SnAgCu solder interconnects under in situ thermal loading, Acta Materialia, 55 (2007) pp 3253-3260.
- [15] McMahon T. J. (2004). Accelerated testing and failure of thin-film PV modules, Progress in Photovoltaics: Research and Applications 12, pp 235-248.
- [16] Kempe M. D., (2006). Modeling of rates of moisture ingress into photovoltaic modules, Solar Energy Material Solar Cells, 90, 2720-2738.
- [17] Miyashita M., Kawai S., Masuda A., (2012). Measuring method of moisture ingress into Photovoltaic modules, Japanese Journal of Applied Physics 51 (2012) 10NF12-1-10NF12-4.
- [18] Wu D., Zhu J., Betts T. R., Gottschalg R., (2014). Degradation of interface adhesion strength within photovoltaic mini-modules during damp-heat exposure, Progress in Photovoltaics: Research and Applications 22 (2014) pp 796-809.
- [19] Park N. C. and al., (2013). Effect of Temperature and Humidity on the Degradation Rate of Multicrystalline Silicon Photovoltaic Module. International Journal of Photoenergy. November 2013, Volume 2013.
- [20] Escobar L. A. and Meeker W. Q., (2006). A review of accelerated test models, Statistical Science, vol. 21, no. 4, pp. 552–577.
- [21] Naah E. Hydrologue, Unesco-PHI: Recherche et développement pour l'environnement en Afrique sub-saharienne.
- [22] Koukpedjé A. A. et al., (2015). Influence de la température, de la pression et de l'humidité relative de l'air sur le potentiel éolien dans la zone côtière du Bénin dans le Golfe de Guinée », Revue des Energies Renouvelables Vol. 18 N°2 (2015) pp 217-226.
- [23] Duffie J. A., Beckman W. A. Solar engineering of thermal processes. Second ed. John Wiley & Sons Inc., New York; 1991.
- [24] King D. L., Quintana M. A., Kratochvil J. A., Ellibee D. E., Hansen B. R. (2000). Photovoltaic module performance and durability following long-term field exposure. Progress in Photovoltaics: Research and Application, 8: pp 241–256.
- [25] Quintana M. A., King D. L., Hosking F. M., Kratochvil J. A., Johnson R. W., Hansen B. R., Dhery N. G., Pandit M. B. (2000) Diagnostic analysis of silicon photovoltaic modules after 20-year field exposure. Proceedings of the 28th PV Specialists Conference, Anchorage, AK, USA; pp 1420–1423.

- [26] Realini A, Burá E, Cereghetti N, Chianese D, Rezzonico S, Sample T, (2001). Ossenbrink H. Study of a 20 year old PV plant (MTBF project). Proceedings of the 17th European Photovoltaic Solar Energy Conference, Munich, Germany; pp 447–450.
- [27] Realini A. (2003) Mean time before failure of photovoltaic modules, Federal Office for Education and Science, Final report BBW 99.0579.
- [28] Reis A. M., Coleman N. T., Marshall M. W., Lehman P. A., Chamberlin C. E. (2002). Comparison of PV module performance before and after 11-years of field exposure. Proceedings of the 29th PV Specialists Conference, New Orleans, LA, USA, pp 1432–1435.
- [29] Sakamoto S., Oshiro T. (2003). Field test results on the stability of crystalline silicon photovoltaic modules manufactured in the 1990s. Proceedings of the 3rd World Conference on Photovoltaic Energy Conversion, Osaka, Japan; pp 1888–1891.
- [30] Hedström J., Palmblad L. (2006) Performance of old PV modules: measurement of 25 years old crystalline silicon modules, Elforsk Rapport 06: 71.
- [31] Saleh I. M., Abouhdima I., Gantrari M. B. (2009). Performance of thirty years stand alone photovoltaic system. Proceedings of the 24th European Photovoltaic Solar Energy Conference, Hamburg, Germany, pp 3995–3998.
- [32] Vignola F, Krumsick J, Mavromatakis F, Walwyn R. (2009). Measuring degradation of photovoltaic module performance in the field. Proceedings of the 38th American Solar Energy Society Annual Solar Conference, Buffalo, NY, USA.
- [33] Eikelboom J. A., Jansen M. J. (2000). Characterisation of PV modules of new generations, results of tests and simulations, Netherlands Energy Research Foundation (ECN), Report code: ECN-C-00-067.
- [34] Lopez-Garcia J. (2017). Lifetime Evaluation of PV Inverters considering Panel Degradation Rates and Installation Sites. Conference Paper.
- [35] Vázquez M, Rey-Stolle I. (2008). Photovoltaic module reliability model based on field degradation studies. Progress in Photovoltaics: Research and Application, 16: pp 419–433.
- [36] Hulkoff T. (2009). Usage of Highly Accelerated Stress Test (HAST) in Solar Module Ageing Procedures. Department of Electrical Engineering Division of Energy and Environment CHALMERS UNIVERSITY OF TECHNOLOGY Göteborg, Sweden.
- [37] Park H., Jeong J., Shin E., Kim S., Yi J. A reliability study of silicon heterojunction photovoltaic modules exposed to damp heat testing, Microelectronic Engineering, July 2019, volume 216.
- [38] Kim H. A., Baeg J. H, Shin J., Park J., Lee S. (2018), Effect of Damp Heat on the Performance Degradation of Flexible CIGS Photovoltaic Modules. Int J Adv Technol 9: 200., Volume 9 doi:10.4172/0976-4860.1000200